

REVIEW ARTICLE

Open Access

Phase-change VO₂-based thermochromic smart windows

Cancheng Jiang¹, Lanyue He¹, Qingdong Xuan², Yuan Liao¹, Jian-Guo Dai³ and Dangyuan Lei¹✉

Abstract

Thermochromic coatings hold promise in reducing building energy consumption by dynamically regulating the heat gain of windows, which are often regarded as less energy-efficient components, across different seasons. Vanadium dioxide (VO₂) stands out as a versatile thermochromic material for smart windows owing to its reversible metal-to-insulator transition (MIT) alongside correlated structural and optical properties. In this review, we delve into recent advancements in the phase-change VO₂-based thermochromic coatings for smart windows, spanning from the macroscopic crystal level to the microscopic structural level (including elemental doping and micro/nano-engineering), as well as advances in controllable fabrication. It is notable that hybridizing functional elements/materials (e.g., W, Mo/SiO₂, TiN) with VO₂ in delicate structural designs (e.g., core-shell, optical cavity) brings new degrees of freedom for controlling the thermochromic properties, including the MIT temperature, luminous transmittance, solar-energy modulation ability and building-relevant multi-functionality. Additionally, we provide an overview of alternative chromogenic materials that could potentially complement or surpass the intrinsic limitations of VO₂. By examining the landscape of emerging materials, we aim to broaden the scope of possibilities for smart window technologies. We also offer insights into the current challenges and prospects of VO₂-based thermochromic smart windows, presenting a roadmap for advancing this field towards enhanced energy efficiency and sustainable building design. In summary, this review innovatively categorizes doping strategies and corresponding effects of VO₂, underscores their crucial NIR-energy modulation ability for smart windows, pioneers a theoretical analysis of inverse core-shell structures, prioritizes practical engineering strategies for solar modulation in VO₂ films, and summarizes complementary chromogenic materials, thus ultimately advancing VO₂-based smart window technologies with a fresh perspective.

Introduction

The escalating demand for energy consumption and the resultant emission of CO₂ have been intensifying the global-warming problem, emphasizing the pressing imperative for energy conservation. Reports indicate that residential buildings are responsible for nearly 30% to 40% of the world's primary energy consumption¹. Hence, there is a significant imperative to enhance the energy efficiency of buildings. Among all building components, windows

are frequently identified as less energy-efficient and requiring greater maintenance², making smart windows an attractive research topic in optics, materials science, and building science. Windows play a crucial role in providing thermal, light, and acoustic comfort³, facilitating vision, air ventilation, photo-protection⁴, prevention of skin cancer⁵, and even influencing biopsychological effects⁶. The design of smart windows should take these aspects into consideration. Sunlight interacts with windows through transmission, reflection, or absorption, depending on their spectral properties in the ultraviolet (UV), visible, and near-infrared (NIR) regions. Consistently high transmittance in the visible spectrum is essential to meet lighting requirements. Indeed, a smart switch alternating between high and low transmittance in the UV and NIR spectral bands is desirable to minimize cooling loads during hot seasons and maximize heat gain

Correspondence: Dangyuan Lei (dangylei@cityu.edu.hk)

¹Department of Materials Science and Engineering, Centre for Functional Photonics, and Hong Kong Branch of National Precious Metals Material Engineering Research Centre, City University of Hong Kong, Kowloon, Hong Kong 999077, China

²Department of Refrigeration and Cryogenics Engineering, Hefei University of Technology, 193 Tunxi Road, Hefei 230009, China

Full list of author information is available at the end of the article

These authors contributed equally: Cancheng Jiang, Lanyue He

© The Author(s) 2024



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

during cold seasons. Thermochromic smart windows adjust radiation in invisible spectra according to surrounding temperatures, paving the way for highly efficient windows in the next generation of energy-conscious architectures.

Currently, commonly utilized thermochromic materials encompass vanadium dioxide, perovskite⁷, organic liquid crystal⁸, as well as mechano-thermo-chromic materials such as supersaturated salt hydrate crystal⁹. While supersaturated salt hydrates offer rapid and reversible phase transitions for smart window applications⁹, VO₂ stands out for its sharp and abrupt change in transparency at a specific temperature, providing precise and consistent performance without the need for mechanical triggers or complex electro-thermal systems. VO₂ is notable for the reversible temperature-dependent dielectric constants, exhibiting significant disparities between their metallic and insulating states. Rutile VO₂(R) undergoes a reversible first-order MIT to monoclinic VO₂(M) at a relatively moderate phase transition temperature (T_c , 68 °C). The structure and optical properties can mutate before and after T_c ^{10–13}, which makes VO₂ an ideal thermochromic material for smart windows over the years.

Here, we provide an overview of phase-change VO₂-based thermochromic coatings for smart windows, drawing on the latest research and structured according to the logic depicted in Fig. 1. Firstly, the spectral transmittance modulation resulting from the MIT of VO₂ in crystalline structures is introduced, as illustrated in Fig. 1a. Further exploration is undertaken into the effects of the MIT on the thermodynamic, electrical, and optical properties of VO₂, elucidated through band structures depicted in Fig. 1b. Secondly, elemental doping is introduced as Fig. 1c illustrates, considering the difference between the actual temperature and T_c . Thirdly, we discuss the micro/nano-engineering (Fig. 1d) in the categories including hybridization, core-shell micro/nanostructure, and multilayer films design, emphasizing on the structural effects for further improving the spectral modulation ability. Next, we review fabrication methods of VO₂-based thermochromic films/coatings, with a specific focus on multi-functionalities, such as stability and emissivity, and the capability of controllable large-scale manufacturing, as depicted in Figs. 1e–1f. Additionally, we briefly introduce and discuss other promising chromogenic materials that can potentially be integrated with VO₂ for smart windows to overcome their intrinsic limitations. Finally, outlooks and perspectives are addressed regarding current challenges and further advancements of VO₂-based thermochromic smart windows.

This review distinguishes itself from previous works through the following unique contributions:

1. We provide a comprehensive categorization of VO₂ doping strategies, shedding light on the doping

mechanism, and emphasizing the crucial NIR-energy modulation capability (ΔT_{NIR}) for smart window applications.


2. We pioneer a theoretical analysis of inverse core-shell structures featuring VO₂ as the shell material, delving into their potential for enhancing solar modulation and offering novel insights for future research.
3. We prioritize practical engineering strategies to boost the solar-energy modulation capabilities of VO₂ films, moving beyond mere descriptions of various VO₂ nanostructures.
4. We offer a comprehensive summary of other chromogenic materials that can complement VO₂ to enhance smart window functionality, providing a broader perspective than previous studies.

These elements inject a fresh perspective into VO₂-based smart window technologies and are critical for further advancing the field.

Temperature-triggered phase change for solar modulation

The MIT in VO₂ is thermally induced, with concomitant alterations in the entropy and heat capacity of the material. In 1971, Dr. John B. Goodenough delineated molecular orbital diagrams grounded in crystal-field theory, as depicted in Fig. 1b¹⁴. Simply, there is a π bond and a π^* anti-bond between the V⁴⁺ and O²⁻ orbitals in VO₂(R). Meanwhile, a $d_{//}$ nonbond is formed between nearby V⁴⁺ orbitals along the crystallographic c axis, which partially overlaps with the unfilled π^* band. Metallic characteristics arise from the overlap between π^* and $d_{//}$ bonds, at which the Fermi level falls, leading to the VO₂(R) with high electron mobility. As the temperature decreases, lattice distortion enhances the π overlap between the V⁴⁺ and O²⁻ orbitals, elevating the energy level of the π^* anti-bond. Concurrently, the interaction between V-V pairs induces the splitting of the $d_{//}$ bonds into $d_{//}$ -bonding and anti-bonding components, resulting in a band gap of ~ 0.7 eV between the π^* and $d_{//}$ -bonding levels.

The presence of a band gap, resulting from the split between the π^* and $d_{//}$ -bonding levels, gives rise to insulating properties in VO₂(M). This band gap acts as a barrier to electron mobility, thereby leading to the manifestation of insulating behavior. While there may be variations between this theoretical proposal and experimental observations, it nonetheless offers valuable insights into the fundamental nature of the MIT in VO₂. The fluctuation in electron mobility during the MIT enables switchable electrical conductivity, a characteristic that finds application in diverse fields such as tunable polarization converters^{15,16}. In metallic VO₂(R), the dielectric constant is considerably lower compared to

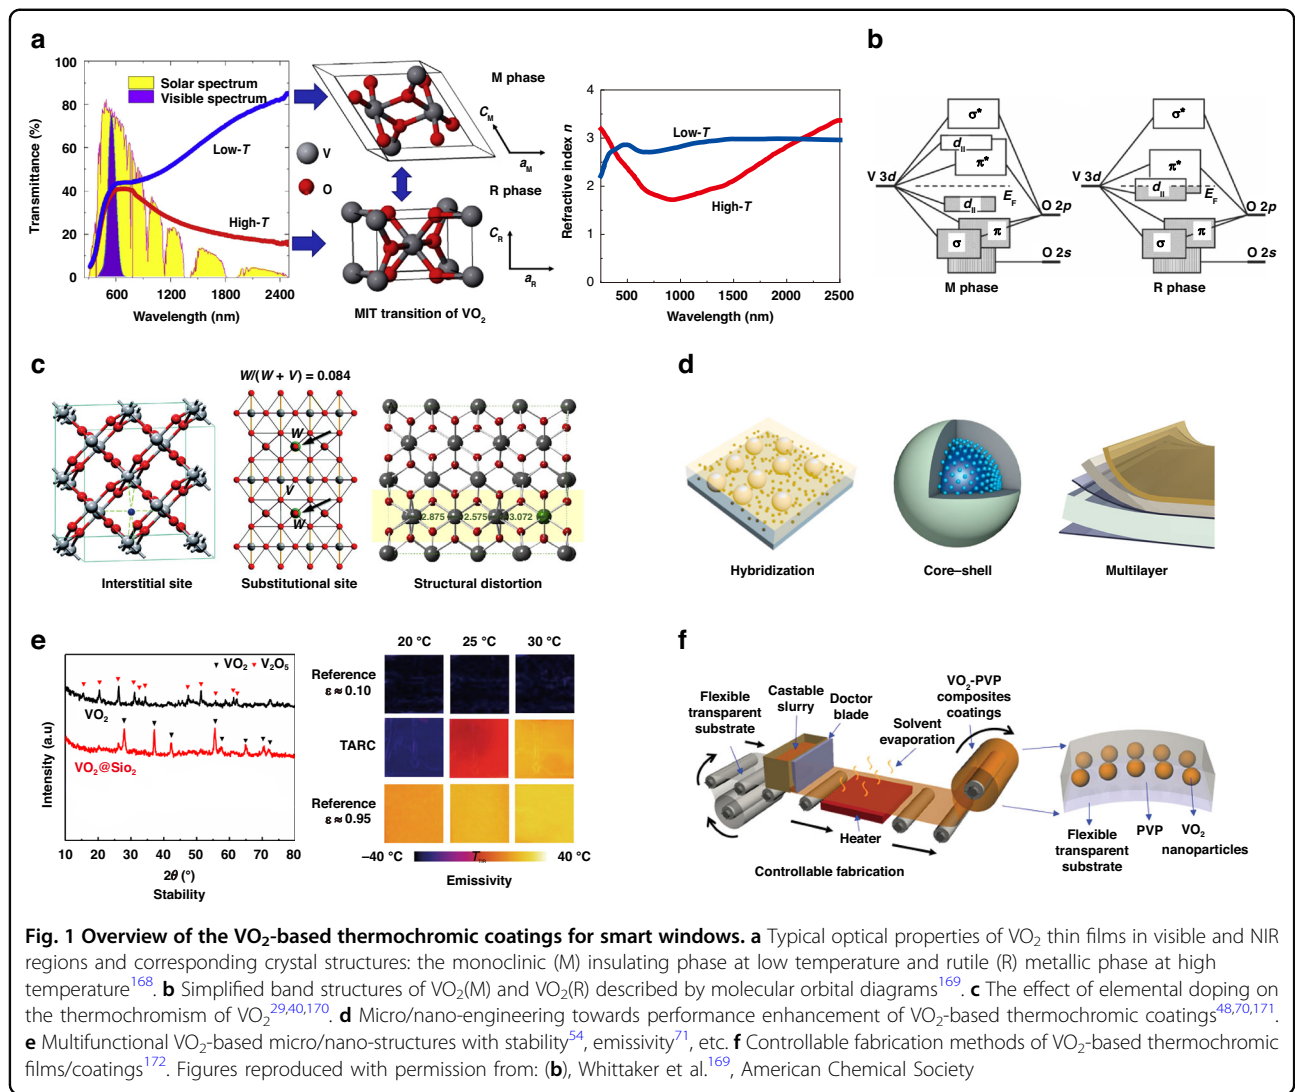

insulating VO₂(M). This discrepancy arises primarily because the presence of free electrons in VO₂(R) allows them to screen the electric field effectively, diminishing the polarization of its lattice structure induced by external electric fields. As a result, the dielectric constant in metallic VO₂(R) is notably reduced in comparison to its insulating counterpart. As depicted in Fig. 1a, VO₂ exhibits a monoclinic structure characterized by high transparency to visible and near-infrared (NIR) light below its phase transition temperature (T_c). Conversely, upon transitioning to the rutile structure (R) above T_c , the material maintains nearly consistent visible light transmittance but experiences a significant reduction in NIR transmittance^{17–20}. To evaluate the optical performance of a VO₂-based thermochromic smart window, the luminous transmittance (T_{lum} , 380–780 nm), the solar-energy modulation ability (ΔT_{sol} , 300–2500 nm) and the NIR-energy modulation ability (ΔT_{NIR} , 780–2500 nm) are

calculated as follow:

$$T_{lum/sol/NIR} = \frac{\int \Phi_{lum/sol/NIR}(\lambda) T(\lambda) d\lambda}{\int \Phi_{lum/sol/NIR}(\lambda) d\lambda} \quad (1)$$

$$\Delta T_{sol} = T_{sol,c} - T_{sol,h} \quad (2)$$

$$\Delta T_{NIR} = T_{NIR,c} - T_{NIR,h} \quad (3)$$

where $\Phi_{lum}(\lambda)$ is the standard luminous efficiency function of human photosensitive vision^{21–23}, $\Phi_{sol/NIR}(\lambda)$ is the solar/NIR irradiance spectrum at air mass 1.5 (corresponding to the sun standing 37° above the horizon)²⁴, $T(\lambda)$ and $T_{lum/sol/NIR}$ denote the spectral transmittance at wavelength λ and luminous/solar/NIR transmittance, respectively. The subscripts lum/sol/NIR and c/h represent the wavelength range (visible/whole solar spectrum/NIR) for integration and thermal states (low temperature/high temperature), respectively.

It's noteworthy that T_{lum} differs from visible solar transmittance (T_{vis})²⁵, which considers the relative spectral distribution of illuminant D65²⁶. For VO₂-based smart windows, ΔT_{NIR} is approximately double ΔT_{sol} , as noticeable spectral transmittance changes occur in NIR bands (~52% of total solar irradiance) before and after MIT. Both high T_{lum} and $\Delta T_{\text{sol/NIR}}$ are crucial: the former signifies better lighting savings, while the latter determines the energy-saving performance of VO₂-based smart windows. However, constrained by the intrinsic MIT, VO₂-based smart windows face obstacles such as high transition temperature (68 °C), low luminous transmittance ($T_{\text{lum}} < 60\%$), and weak solar-energy modulation ($\Delta T_{\text{sol}} < 15\%$). Extensive efforts have been dedicated to addressing these challenges and advancing VO₂-based smart windows for practical applications.

Elemental doping for tailoring the phase-transition temperature

As mentioned above, the primary challenge faced by VO₂-based smart windows in practical applications is the significantly higher MIT compared to the normal operating temperature of conventional windows. To address this issue, researchers commonly employ elemental doping as the primary strategy to modulate T_c and optical properties of VO₂. The effects of some doping elements are summarized in Table 1.

The fundamental role of dopants is to lower the energy barrier, thereby reducing the MIT temperature, as the electronic phase transition in VO₂ nearly coincides with the structural phase transition^{27,28}. Correspondingly, the selection of the elemental doping is commonly based on two key factors: (1) Increasing the carrier concentration to accelerate the electronic phase transition: Dopants are selected to either donate additional electrons (n-type doping) or create spaces for electrons through the formation of vacancies (p-type doping). This tactic increases the mobile charge carrier density within the VO₂ lattice, thereby amplifying the likelihood of electronic excitations that can precipitate the phase transition. By bolstering the number of available charge carriers, the dopants accelerate the electronic phase transition. This acceleration is due to the heightened probability of electronic interactions that can drive the system across the phase boundary, effectively diminishing the energy threshold for the MIT; (2) Introducing distortion into the atomic structure to assist the structural phase transition: The second prong of the doping strategy involves the deliberate introduction of atomic-scale distortions. These distortions arise from the mismatch between the dopants and the host VO₂ lattice in terms of size or valence, leading to localized strain. Such strain can perturb the equilibrium of interatomic forces within the crystal, thus lowering the energy required for the structural reconfiguration that accompanies the MIT. The dopants act as a catalyst for structural changes by stabilizing

the high-temperature metallic phase, which is characterized by a distinct arrangement of V-V dimers. This stabilization aids in the rapid reorganization of the vanadium and oxygen atoms, facilitating the transition from the insulating to the metallic state.

Regarding the increase in carrier concentration, researchers have pursued two primary doping strategies: a) insert smaller-sized doping atoms (Fig. 1c, left) such as H^{29,30}, Li^{31,32}, Na^{31,33}, and B^{34,35} into the interstitial sites of VO₂; b) substitute the V sites with high-valence elements (Fig. 1c, mid) such as W^{36,37}, Mo³⁸, Nb³⁹. These strategies aim to enhance the concentration of mobile charge carriers within VO₂ crystals, thus lowering T_c . For instance, when smaller dopant atoms are inserted into the interstitial sites of VO₂ lattice, they introduce additional electrons, thereby increasing the carrier concentration within VO₂ crystals. Similarly, by substituting vanadium sites with high-valence elements, these elements can inject partial electrons into the valence band of VO₂. For example, by substituting vanadium atoms in VO₂, tungsten atoms can inject electrons into the valence band of VO₂, effectively lowering T_c , typically by 20–26 K/at%.

On the other hand, to address structural distortion, researchers have also employed methods such as adjusting the V-V distances in VO₂ or modifying lattice parameters by a dopant (Sb⁴⁰, Be⁴¹, etc.). Through these measures, researchers can effectively modulate the crystal structure of VO₂, thereby affecting its transition temperature T_c . For example, by adjusting the distances between vanadium atoms in VO₂ crystals or by modifying lattice parameters, the structure of VO₂ crystals can be altered to facilitate phase transition. These adjustments and distortions in structure can effectively reduce the transition temperature T_c of VO₂, making it more suitable for applications such as smart windows.

In conclusion, elemental doping serves as an effective method for modulating the critical transition temperature of VO₂-based smart windows, with selection based on precise control of carrier concentration and structural distortion. This strategy provides crucial technical support for enhancing the performance and applicability of VO₂-based smart windows in practical applications. In future research, a deeper understanding of the doping mechanism and various influencing factors in the doping process will be essential.

While doping strategies have been successful in modulating the transition temperature (T_c), the environmental stability and long-term performance impact of doped elements must be considered. Greater emphasis should be placed on the selection of dopants and the optimization of doping levels in future research to ensure more stable and efficient thermochromic smart windows.

Table 1 Elemental doping effects on the thermochromic performance of VO₂-based films

Doping strategies (chemical formula)		Dopant(s)	Doping level (at%)	T _{lum} (%)	ΔT _{sol} (%)	ΔT _{NIR} (%)	dT _c /dx (°C/at%)	T _c (K)	Ref.
Carrier concentration increase	Interstitial site (VA _x O ₂)	H	3	-	-	-	-38	227	29,30
		Li	3	-	-	-	-43	212	31,32
		Na	3	-	-	-	-49	293.15	31,33
		B	6	54.3	12.5	27.8	-63.3	301.25	34,35
	Substitutional site (V _{1-x} A _x O ₂ /V _{1-x-y} A _x B _y O ₂)	W	2	50.7	8	18.2	-20	301	36,37
		Mo	3	34.5	1.1	2.5	-9.33	313.01	132,133
		Nb	2.5	38.8	2.6	6.6	-8.4	320	134,135
		Sr + W	11.9 + 0.9	61.8	5.2	10	-	-	136,137
		Zr + W	4.2 + 2.1	60.7	10.6	22.7	-21.1	-	138,139
		Mo + W	7 + 8	55	-	-	-6.47 to 6.7	-	140,141
Structural distortion (VA _x O ₂ /V _{1-x} A _x O ₂)	Sn + W	1.9 + 1.6	41.1	13.4	25.7	-	-	142,143	
	Sb	7	-	-	-	-11.7	259.1	40,144	
	Be	3	-	-	-	-58	-	41,145	
	Cr	3	22.4	7.4	19.1	0.69	343.07	146,147	
	Ru	2.32	-	-	-	-10.5	316.64	148,149	

"-" means data unavailable


Micro/nano-engineering for Improving the solar-energy modulation ability

In addition to lowering T_c, elevating T_{lum} and ΔT_{sol} is also important for smart window applications⁴². Micro/nano-engineering strategies through either micro- or macro-structural/materials modification have been proposed and investigated widely⁴³. According to the modification principles, the reported micro/nano-engineering strategies can be classified into three categories: 1) hybridization that incorporates other materials/structures with individual VO₂ materials, 2) core-shell micro/nano-structures that modulate the Mie/plasmonic resonant responses of spherical VO₂ nanoparticles (NPs) as either core or shell, and 3) multilayer films that integrate other flat layers for enhanced optical resonances as well as multifunctionality.

VO₂-based hybridized thin films

In efforts to improve the thermochromic properties of VO₂-based thin films, researchers often encounter a trade-off between ΔT_{sol} and T_{lum} when using thick layers of continuous VO₂ film. To address this challenge, hybridization with other inorganic and/or organic materials has emerged as a viable strategy to optimize both T_{lum} and ΔT_{sol} simultaneously. This hybridization approach may affect the MIT and hysteresis-loop width of VO₂ by inducing strains, while also modulating optical constants such as T_{lum} and color⁴⁴. Furthermore, the

introduction of functional materials like TiO₂⁴⁵ and ZrO₂⁴⁶ can add multifunctionality to the composite films, offering benefits such as self-cleaning and mechanical reinforcement. Researchers have explored various strategies to improve the optical performance of VO₂-based thin films. Li et al. theoretically investigated the optical performance of VO₂ NPs matrix composites and yielded much higher T_{lum} and ΔT_{sol} than pure VO₂ thin films by calculations based on effective medium theory⁴⁷. Liang et al. further introduced SiO₂ microparticles in the W-doped VO₂/PVP composites for T_{lum} improvement. The single layer of randomly dispersed SiO₂ microspheres in the film provided optical pathways for sunlight, which offset the decrease of T_{lum} caused by the strong absorption of visible light by high volume concentration of W-VO₂ NPs (Fig. 2a). Experimental results revealed that W-doped VO₂/SiO₂/PVP composite films enable high T_{lum} of 65% without sacrificing too much ΔT_{sol} (12.6%)⁴⁸, which also proved the validity of the structure in the previous study by Li et al.⁴⁷. Hao et al. proposed an alternative strategy that utilize plasmonic response to balance T_{lum} and ΔT_{sol}. A plasmonic array of TiN NPs was fabricated underneath the VO₂ thin film as Fig. 2b exhibits and endowed ΔT_{sol} of 10.8% and T_{lum} of 51%, respectively⁴⁹. TiN NPs can efficiently absorb NIR radiation to provide local heating and accelerate the MIT in VO₂. Additionally, the VO₂ film can also be patterned for performance improvement. Cao et al. synthesized

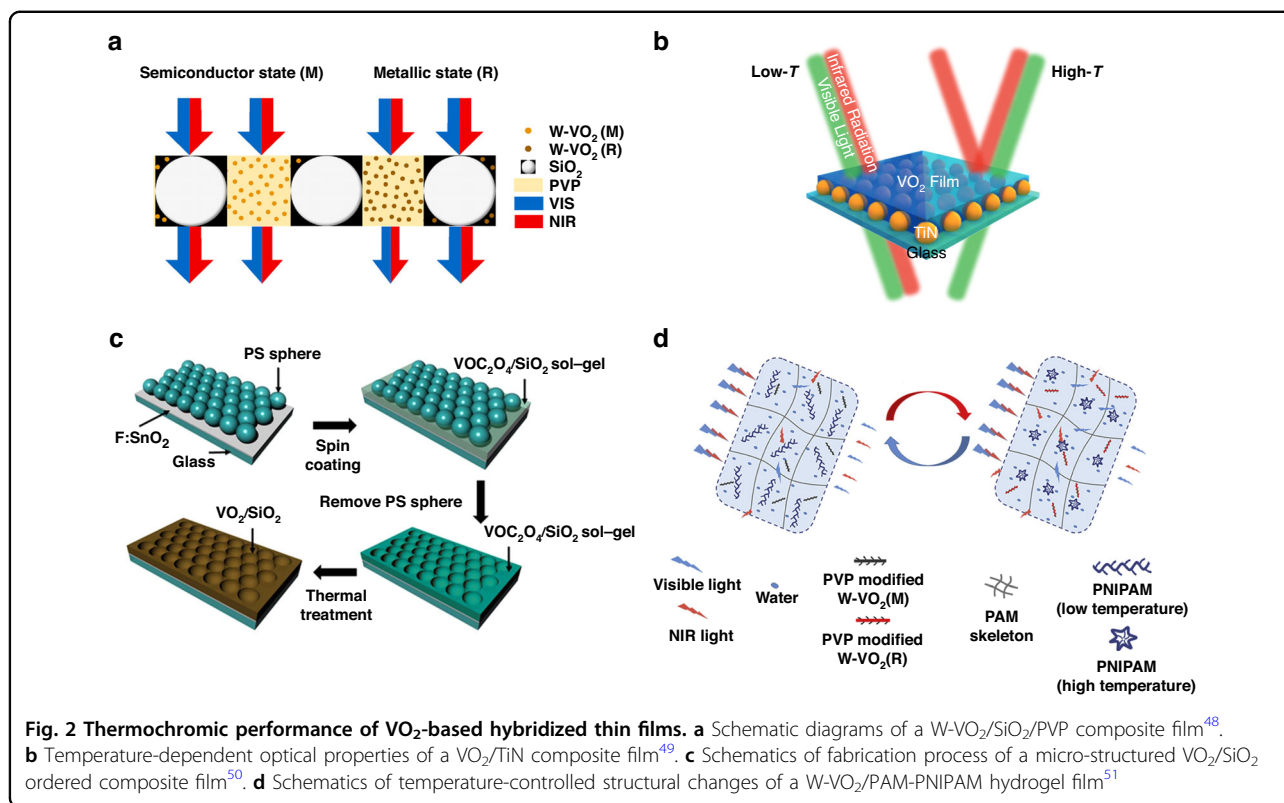

periodical and spherical cavity-structured VO₂/SiO₂ composite films through a polystyrene template and annealing process as illustrated in Fig. 2c. Under the photonic crystal structure of the patterned VO₂ composite film, balanced thermochemical properties can be obtained as ΔT_{sol} of 8.4% and T_{lum} of 55.6%⁵⁰. Inorganic VO₂ could also be integrated with organic materials to enhance the thermochemical properties. For instance, He et al. presented a dynamically regulated system based on W-VO₂/PAM-PNIPAM hydrogel films, which was developed into smart windows (ΔT_{sol} 46.3% and T_{lum} 72%)⁵¹. As illustrated in Fig. 2d, the PVP-modified monoclinic W-VO₂ was dispersed in the PNIPAM microgel, where the PAM hydrogel with high T_{lum} serves as a skeleton, holding and keeping water molecules, PNIPAM microgel and surface-modified W-VO₂ inside. Upon heating, the intramolecular and intermolecular hydrophobicity of PNIPAM is enhanced, leading to the discharge of water molecules from the chemical framework of PNIPAM and generating phase separation interfaces. These interfaces can strongly scatter the incident solar irradiance when the W-VO₂ undergoes the MIT and hence dramatically enhance the NIR light reflectivity simultaneously.

VO₂-based core-shell micro/nano-structures

In addition to hybridization methods, core-shell approaches have emerged as an efficacious strategy for

enhancing the thermochemical properties and functionalities of VO₂-based films⁵². These core-shell nanostructures can be broadly categorized into bilayer and trilayer configurations based on the number of layers, wherein VO₂ is encapsulated within dielectric shells such as SiO₂, TiO₂, SnO₂, ZnO, Al₂O₃⁵³, or metallic shells like Au and Ag. For instance, Pi et al. prepared thermochemical and hydrophobic core-shell VO₂@SiO₂ (VSQ) NPs with tetraethoxysilane (TEOS) and dimethyloctadecyl [3-(trimethoxysilyl) propyl] ammonium chloride (DMOAP) as depicted in Fig. 3a⁵⁴. The ΔT_{sol} reaches up to 15.4% while the T_{lum} remains as high as 51.5% owing to localized surface plasmon resonance (LSPR)⁵⁵. Furthermore, the SiO₂ shell efficiently shields VO₂ from oxidation, enhancing its durability, while DMOAP modification imparts additional functionalities including anti-agglomeration, surface hydrophobicity, and self-cleaning, as illustrated in Fig. 3b⁵⁴. Lu et al. synthesized VO₂@SiO₂@Au trilayer core-shell nanoparticles to harness LSPR and enhance optical tunability, as depicted in Fig. 3c⁵⁶. By modulating the material composition and particle sizes of the outer metallic shell, the resonance peak could be tuned across a wide spectral range, offering customizable colorful appearances for the films, as shown in Fig. 3d. Since VO₂ can transition between dielectric and metallic states, it can be employed as either the inner or outer layer of core-shell structures. Yao et al. fabricated SiO₂@TiO₂@VO₂ inverted trilayer core-shell NPs via

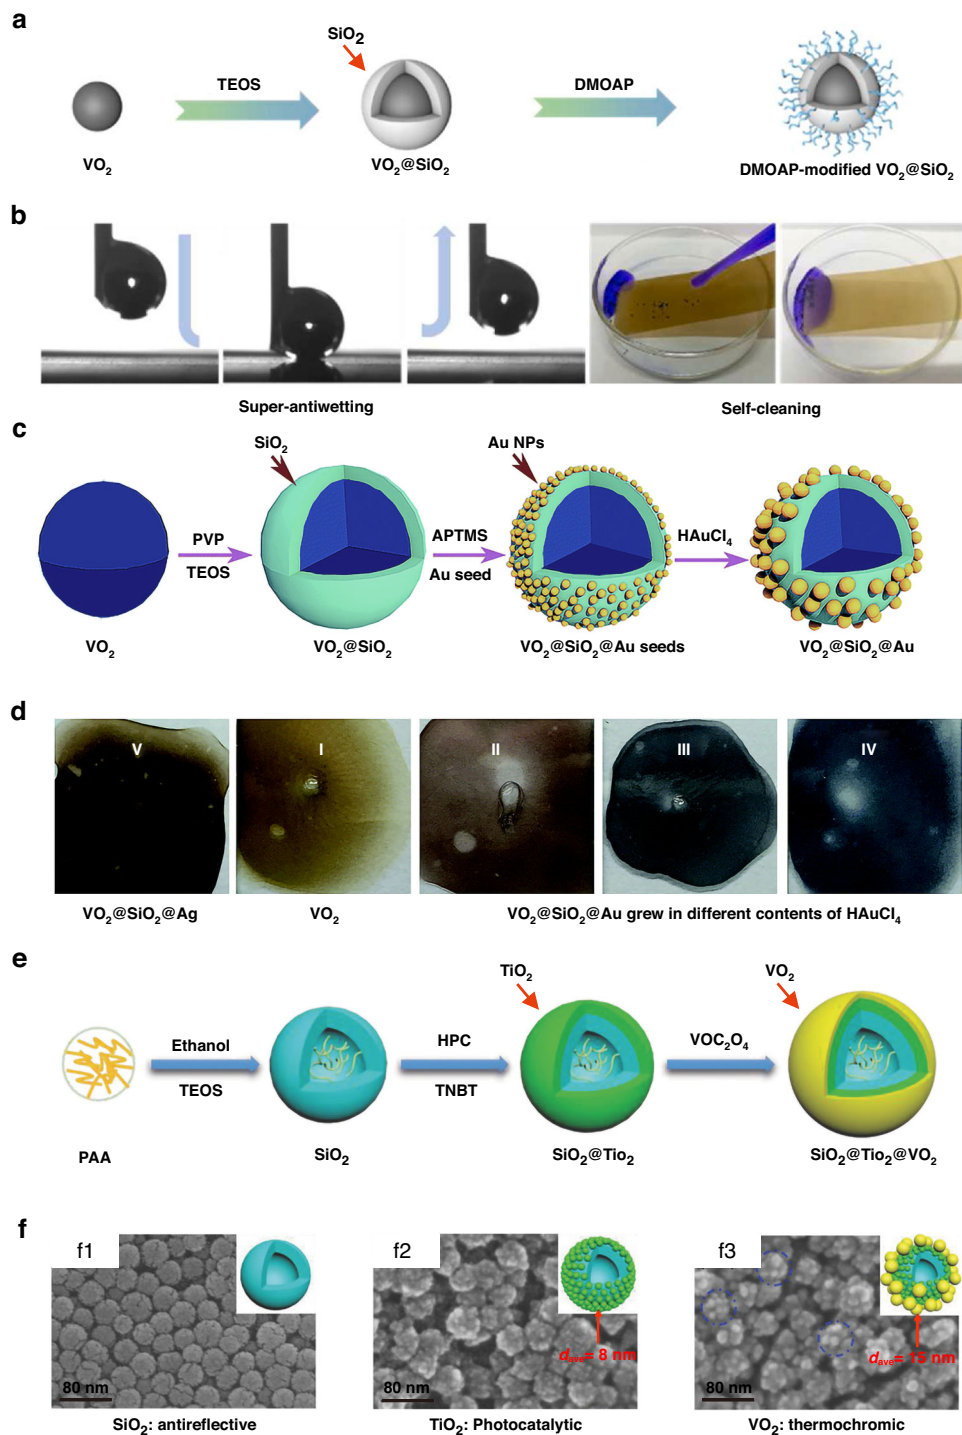


Fig. 3 Thermochromic performance of VO₂-based core-shell micro/nanostructures. **a** Synthesis procedures of VSQ core-shell NPs⁵⁴. **b** Low water adhesion and self-cleaning performance of a VSQ-coated surface⁵⁴. **c** Synthesis procedures of VO₂@SiO₂@Au trilayer core-shell NPs⁵⁶. **d** Different colors of VO₂-based trilayer core-shell NPs-based films. From left to right: a VO₂@SiO₂@Ag NPs-based film (V), a plain VO₂ film (I), VO₂@SiO₂@Au films grew in different content of HAuCl₄ (II-IV)⁵⁶. **e** Synthesis procedures of SiO₂@TiO₂@VO₂ inverted trilayer core-shell NPs⁵⁷. **f** SEM micrographs of (f1) a SiO₂ hollow nanosphere-based coating, (f2) a SiO₂@TiO₂ coating, and (f3) a SiO₂@TiO₂@VO₂ coating, respectively⁵⁷

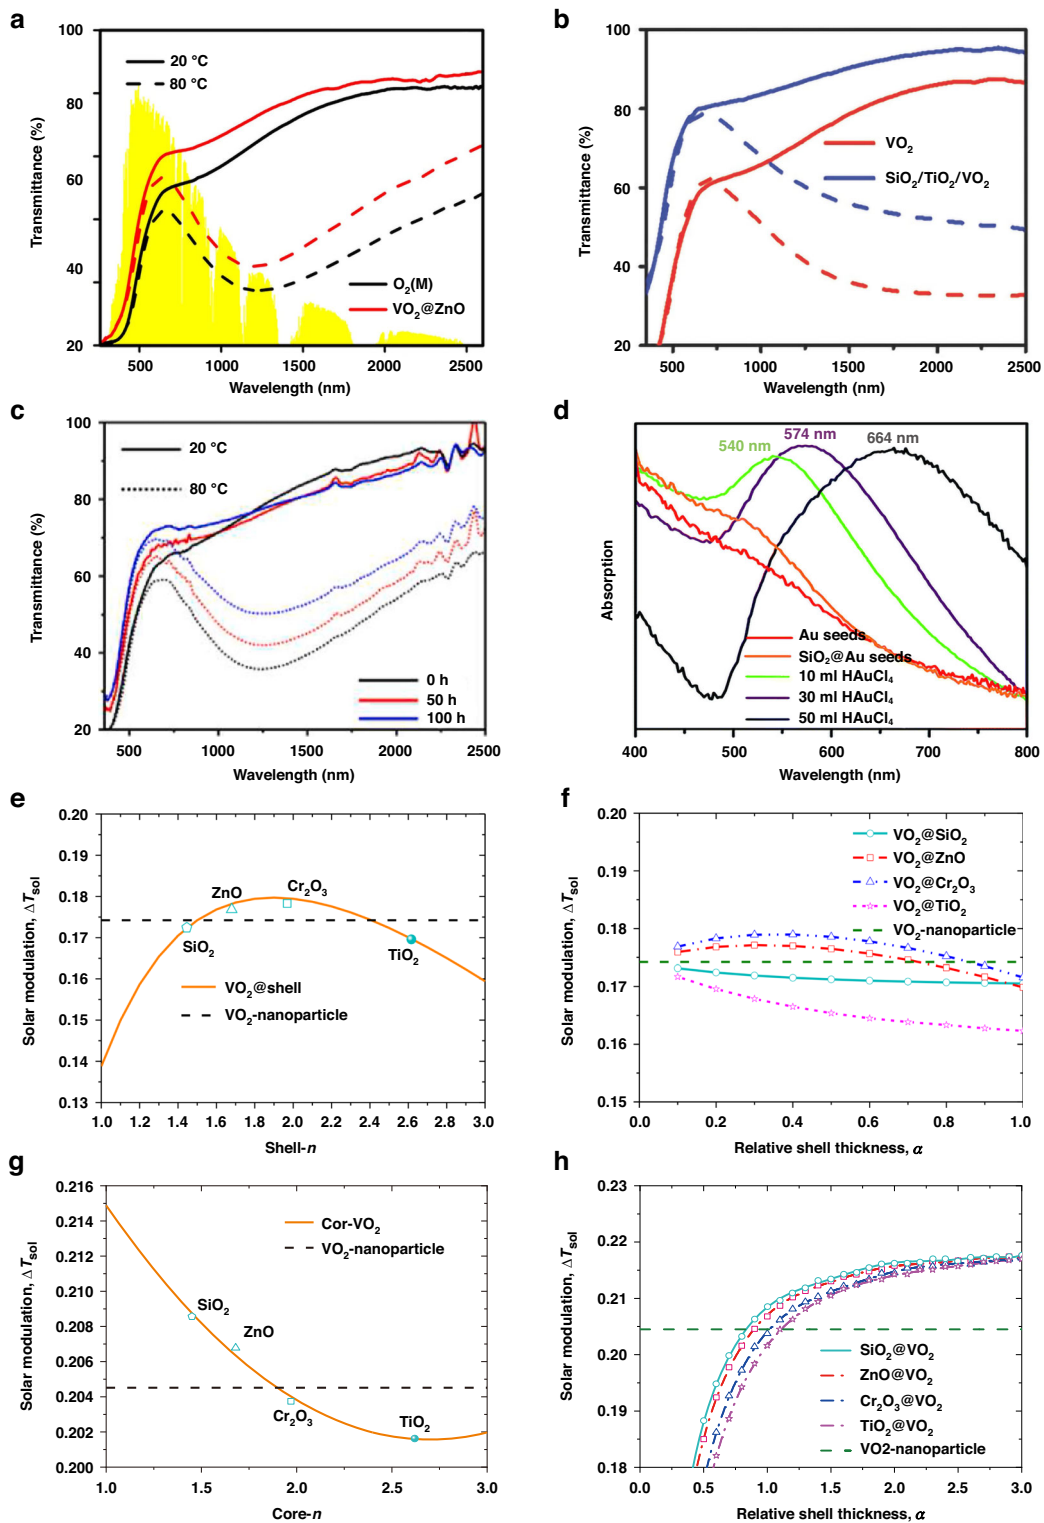


Fig. 4 Optical and thermal performance of VO₂-based films and coatings. **a–c** Transmittance spectra of **a** VO₂ and VO₂@ZnO films at 20 and 80 °C¹⁷³, **b** VO₂ and SiO₂@TiO₂@VO₂ coatings at 20 and 100 °C⁵⁷, and **c** VSQ coatings treated at 60 °C and 90% RH for different periods⁵⁴. **d** Absorption spectra of different solutions⁵⁶. **e, f** ΔT_{sol} of VO₂ core-shell NPs-based films, as a function of **e** shell refractive index and **f** relative shell thickness⁵³. **g, h** ΔT_{sol} of VO₂ inverted core-shell NPs-based films, as a function of **g** core refractive index and **h** relative shell thickness, the performance of the plain VO₂ film was shown by the dashed lines. Figures reproduced with permission from: **a**, Chen et al.⁵⁸, American Chemical Society

controlled interfacial engineering, as depicted in Fig. 3e. The T_{lum} of the resultant coating reached a remarkable 74%. Additionally, as Fig. 3f illustrates, since TiO_2 was partially exposed rather than completely covered by VO_2 , the coating facilitated the integration of thermochromism from the outer VO_2 layer, photocatalytic self-cleaning capability from the middle TiO_2 layer, and antireflective properties from the internal SiO_2 hollow nanospheres⁵⁷.

The spectral transmittances of typical bilayer and trilayer VO_2 -based core-shell structures are shown in Fig. 4a, b, demonstrating a notable enhancement in T_{lum} . Additionally, Fig. 4c, d illustrates the durability and coloration of these core-shell configurations, providing detailed insights into their multifunctional capabilities. Specifically, Fig. 4c showcases the VSQ coating’s ability to enhance the stability and longevity of VO_2 by providing a protective SiO_2 shell, preventing oxidation, incorporating hydrophobic modification for self-cleaning, and maintaining structural integrity through robust adhesion. This innovative approach collectively improves environmental and mechanical durability, addressing crucial challenges faced by VO_2 -based thermochromic coatings⁵⁵. Moreover, in Fig. 4d, the tunable SPR properties of Au nanoparticles are highlighted, demonstrating their potential to modify the color of solutions and, by extension, the color of VO_2 -based thermochromic smart films⁵⁷. Lu et al.’s work illustrates how controlling the size of the Au nanoparticles enables the tailoring of film color from brick red to purple and blue. This advancement represents a significant stride in the development of smart window technologies, offering versatile solutions for enhancing the aesthetic appeal and functionality of VO_2 -based coatings. The thermochromic behavior of VO_2 -based core-shell structures is intricately linked to the properties of the core/shell materials and their respective sizes, which govern the dielectric environment surrounding VO_2 ⁵⁴. To systematically investigate the optical performance of the thermochromic films, Xie et al.

performed theoretical calculations based on the effective medium theory coupled with the transfer matrix method. Their findings, showcased in Fig. 4e–f, suggest that for films composed of VO_2 core-shell nanoparticles, selecting a low absorption shell material (e.g., ZnO or Cr_2O_3) with a refractive index (RI) ranging from 1.6 to 2.3, and maintaining a relative shell thickness between 0.1 and 0.3, is crucial for preserving a high sol-gel transition temperature difference (ΔT_{sol})⁵³. Here, the relative shell thickness (α) is defined as the ratio of the shell thickness to the core radius ($\alpha = t_{shell} / R_{core}$). In Fig. 4e, dashed lines represent the solar modulation capability of VO_2 nanoparticle, while solid orange lines represent $VO_2@shell$ structures with varying shell materials. Analysis indicates that VO_2 -based core-shell structures outperform VO_2 nanoparticles when the shell refractive index falls within 1.6 to 2.3, yielding performance enhancement. Similarly, in Fig. 4f, for $VO_2@ZnO$ or $VO_2@Cr_2O_3$ structures, superior performance of VO_2 -based core-shell structures is observed with shell thickness between 0.1 and 0.3, demonstrating performance improvement. Table 2 has been included, detailing the distinct performance and characteristics of VO_2 -based core-shell micro/nanostructures with various dielectric and metallic shell materials.


However, the scarcity of investigations into the optical characteristics of inverted core-shell structures, where VO_2 serves as the shell material, underscores a critical gap in our current understanding. To address this gap, we conducted theoretical analyses utilizing the Mie theory coupled with the Monte Carlo method. Our research specifically targeted inverted VO_2 core-shell nanoparticles incorporating core materials such as SiO_2 , ZnO, Cr_2O_3 , and TiO_2 .

Upon scrutinizing Fig. 4e, g, a notable trend emerged: the inverted structures consistently displayed superior solar modulation capability across all material combinations compared to their conventional counterparts. Furthermore, it was observed that the ΔT_{sol} of these films

Table 2 Performance comparison of different VO_2 core-shell structures

No.	Core Material	Shell Material	T_{lum} (%)	ΔT_{sol} (%)	Characteristics/Performance	Ref.
1	VO_2	SiO_2	51.5	15.4	High weatherability, high ΔT_{sol} and T_{lum}	55
2	VO_2	$SiO_2@Au$	-	7.52	Trilayer core-shell structure, high optical tunability	57
3	SiO_2	$Au@VO_2$	74	12	Inverted trilayer core-shell structure, high thermochromism benefiting from partially exposed TiO_2	58
4	VO_2	ZnO	-	-	Low absorption shell material, high ΔT_{sol}	54
5	VO_2	Cr_2O_3	-	-	Low absorption shell material, high ΔT_{sol}	54
6	VO_2	SiO_2	51.5	15.4	Metallic shell, high LSPR effect	56
7	VO_2	Ag	-	-	Metallic shell, high LSPR effect	56

“-” means data unavailable

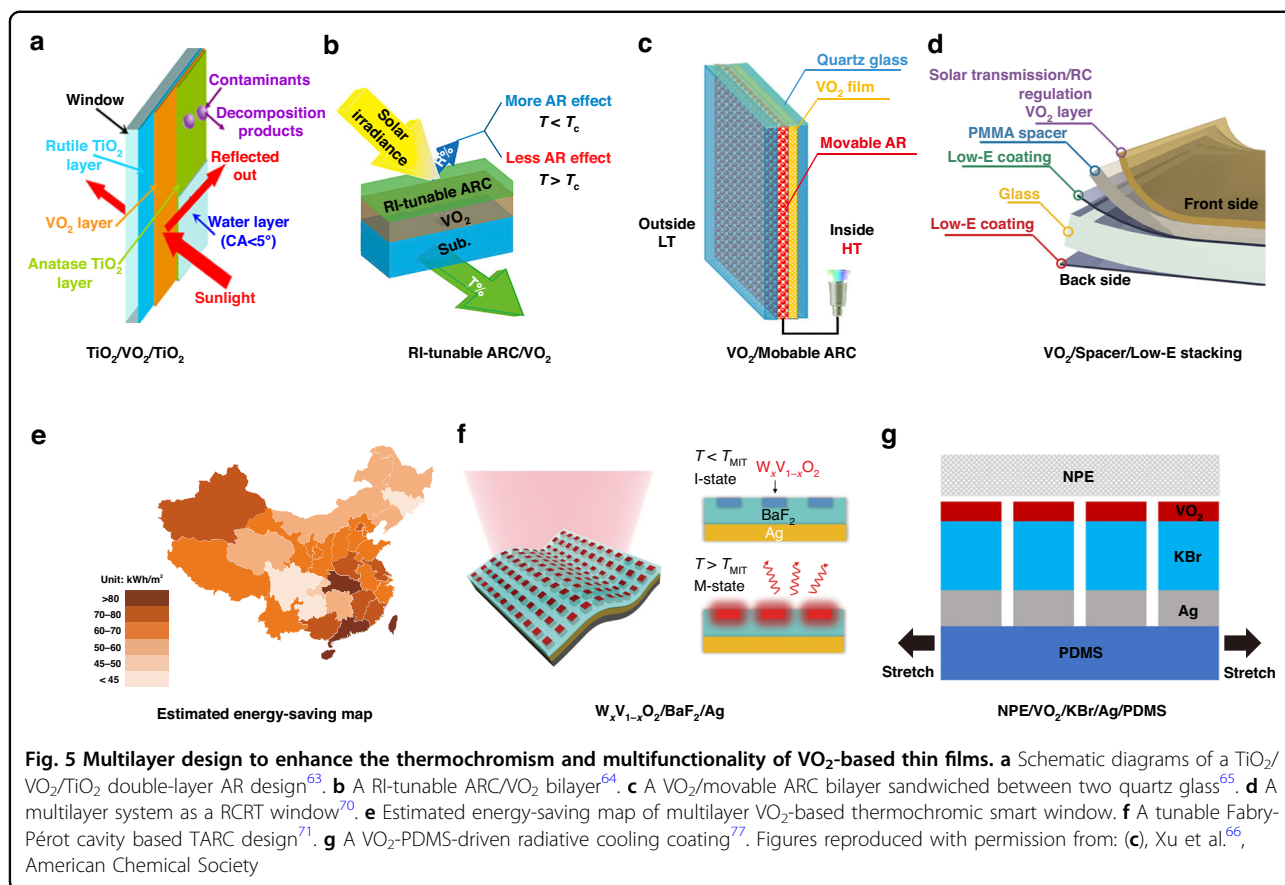

could be further enhanced by integrating low-absorption core materials, like SiO₂, characterized by a low refractive index and a relative shell thickness exceeding 1.1, as shown in Fig. 4g, h. These results reveal that the inversion of the core-shell structure leads to enhancements in Mie scattering effects, suggesting that inverted structures hold greater potential for solar modulation capabilities compared to ordinary structures.

Multilayer films design with photonic cavity

In general, there are mainly two forms of thermochromic coatings based on VO₂: flexible foils and multilayered films. Flexible foils involve dispersing VO₂-based nanoparticles in a polymer host matrix such as PU, PVP, and PMMA, and then combining them with a flexible substrate. On the other hand, multilayered films are typically fabricated on glass using direct deposition methods such as physical vapor deposition (PVD) and chemical vapor deposition (CVD). Since the absorption of VO₂ is mainly in the 250–700 nm wavelength range, the T_{lum} of single-layer VO₂ films is generally restricted. Additionally, due to its transmittance switches primarily in the NIR region, which accounts for about 43% of solar energy in the solar spectrum, leading to limited solar modulation (ΔT_{sol}), often remaining below 10%.

Multilayer films design is an effective solution towards this perplexity. To address these limitations, multilayer film designs have emerged as effective solutions. These films not only allow for the design of solar transmittance but also enable the tailoring of NIR emissivity⁵⁸. Moreover, the integration of different layers makes it easier to achieve multifunctionality compared to single-layer films.

Antireflection (AR) is a noteworthy function that has been demonstrated as a viable method to enhance the low luminous transmittance (T_{lum}) of VO₂-based films without compromising their thermochromic properties. Additionally, neat VO₂ is prone to oxidation to V₂O₅ in air and exhibits poor acid resistance, leading to environmental instability that limits its practical application as a thermochromic coating in smart windows⁵⁹. Incorporating VO₂ films with other layers can introduce practical functions such as antioxidizability⁶⁰, hydrophobicity⁶¹, and photocatalysis⁶². For instance, Zheng et al. designed a TiO₂/VO₂/TiO₂ multilayer film (with ΔT_{sol} of 10.2% and T_{lum} of 30.1%), which exhibited at least three functions: antifogging/self-cleaning, thermochromic, and antireflective properties. These properties were respectively attributed to the top TiO₂(A), the middle VO₂(M), and the bottom TiO₂(R) layers, as illustrated in Fig. 5a⁶³. However, as for the antireflection coatings (ARCs), most

researchers focused on increasing luminous transmittance (T_{lum}) at the expense of sacrificing solar modulation (ΔT_{sol}). This trade-off is a significant challenge as ΔT_{sol} is a determinant factor for energy-saving applications and can hinder the translation of these technologies from the laboratory to the market. To address this challenge, variable ARC/VO₂ multilayer film designs, as illustrated in Fig. 5b and c, have emerged. For example, Liu et al. utilized a novel RI-tunable (1.47–1.92 at $\lambda = 550$ nm) nano sol-gel-based ARC/VO₂ bilayer (Fig. 4b) with a ΔT_{sol} of 18.9% and T_{lum} of 44% to enhance the antireflective effect at lower temperatures. This approach aims to maximize ΔT_{sol} for various VO₂ nanosubstrates⁶⁴. Xu et al. fabricated a VO₂/Movable ARC bilayer controlled by dual modes using magnetron sputtering, as illustrated in Fig. 5c. This approach significantly improved the thermochromic properties, with a ΔT_{sol} of 18.2% and T_{lum} of 42.5%. Moreover, it enabled the two-phase smart regulation of eco-friendly H₂O through the conversion of liquid and gaseous states. This bilayer system can passively modulate according to the variation in temperature difference between indoor and outdoor environments. Additionally, it can actively control the amount of solvent by detecting the temperature difference and humidity between the insulating glass, thereby adjusting the thickness of the ARC⁶⁵.

Thermal emissivity (ϵ_T) holds equal importance alongside ΔT_{sol} and T_{lum} for VO₂-based smart windows. It has been leveraged in numerous thermal management and energy-saving applications^{66–69} and has recently garnered attention in the context of smart windows, particularly in combination with the concept of radiative cooling^{70–72}. Radiative cooling harnesses the infrared atmospheric transparent window to dissipate heat and effectively cools terrestrial objects through thermal radiation^{73–75}.

In comparison to traditional smart windows, which primarily focus on modulating incoming solar energy, high thermal emissivity (ϵ_T) for radiative cooling offers an additional channel for dissipating excessive thermal energy generated by solar heating. According to Kirchhoff's thermal law, the absorptivity of an object is equal to its emissivity in thermal equilibrium conditions. And the transmittance of glasses can be ignored when the wavelength is longer than 4.5 μ m. Commonly, ϵ_T is calculated by weighting the film reflectance with the black-body emission spectrum from 4.5 to 25 μ m as follow:

$$\epsilon_T = \sum_{4.5}^{25} G_T(\lambda)E(\lambda)\Delta\lambda \approx 1 - \sum_{4.5}^{25} G_T(\lambda)R(\lambda)\Delta\lambda \quad (4)$$

where $G_T(\lambda)$ is the normalized relative spectral distribution of black-body radiation at temperature T (T is chosen to be 20 °C according to CNS GB/T 1895.2–2002). $E(\lambda)$ refers to the spectral emittance, i.e., the fraction of the

black-body radiation. $R(\lambda)$ refers to the reflectance in the region (4.5–25 μ m).

A high value of ϵ_T indicates an intensive energy exchange between the window surface and its ambience through thermal radiation and absorption⁷⁶. Wang et al. developed a passive radiative cooling regulating thermochromic (RCRT) smart window (ΔT_{sol} 17% and T_{lum} 32.2%) with tunable long-wave infrared (LWIR) emissivity (ϵ_{LWIR}) based on a W-doped VO₂-PMMA/spacer/low-E stack using spin coating, as illustrated in Fig. 5d. This configuration formed a Fabry-Pérot resonator, enabling the promotion of radiative cooling during warm weather (high ϵ_{LWIR}) or suppress it during cold weather (low ϵ_{LWIR})⁷⁰.

To further elucidate the energy-saving benefits of VO₂-based smart windows, we calculated the annual total energy savings for model buildings equipped with multilayer VO₂-based smart windows ($\Delta T_{sol} = 10\%$, $\Delta\epsilon = 0.5$). Figure 5e illustrates the total energy saved annually in various cities across China. From the energy-saving map, it is evident that cities in southern regions exhibit more pronounced energy-saving effects compared to those in northern regions, primarily due to the hotter climate. For instance, the average annual energy savings in Hong Kong amount to 80.16 kWh/m², whereas in Jilin, it is only 45.12 kWh/m². This analysis underscores that the installation of VO₂-based smart windows in buildings leads to reduced energy consumption, yielding significant energy-saving benefits.

It is worth noting that achieving dynamic modulation of emissivity can be challenging when incorporating low-E coatings (such as ITO) due to their strong NIR blocking properties, which can lead to relatively low values of ΔT_{sol} . The simultaneous modulation of the spectral performance in both the NIR and long-wave infrared (LWIR) regions remains a question to be addressed in future research.

Additionally, Tang et al. introduced a W_xV_{1-x}O₂-based temperature-adaptive radiative coating (TARC), as shown in Fig. 5e, to achieve strong sky-window radiative cooling at high temperatures and solar heating or warm-keeping at low temperatures. This was made possible by amplified radiative absorption facilitated by the designed Fabry-Pérot resonance with adjacent W_xV_{1-x}O₂ blocks, as well as the bottom Ag layer within the $\frac{1}{4}$ -wavelength cavity⁷¹. Furthermore, Liu et al. presented a VO₂-PDMS-driven intelligent radiative cooling coating with both automatic cooling switching and continuous adjustment of thermal comfort, as illustrated in Fig. 5f⁷⁷. The polydimethylsiloxane (PDMS) substrate could be stretched to modulate the radiative cooling power according to our desired cooling temperature. Adjusting the VO₂-PDMS coatings through stretching modifies the filling ratio, consequently influencing the dielectric characteristics of the stacked nano-grating structure. This alteration impacts surface waves at the interfaces, resulting in modifications to the spectral performance of the coatings.

Table 3 Summary of the preparation methods of VO₂ particles

Reaction environment	Method	Pros	Cons	Particle size	Particle shape	Ref.
Solid phase reaction	Thermal reduction	Low-cost, large-scale	Toxicity of reactant, conditional reaction, impurities	Micro	Rhombohedral	150,151
	Pyrolysis	Mild reaction, controllable composition, less impurities	CO ₂ emission, large particle size	Nano	Rod	152,153
Gas phase reaction	Ball-milling	Large-scale, modifiable	Introducing impurities	Nano	Irregular	154,155
	Physical vapor deposition	Morphological control	Conditional reaction	Micro/nano	Rod	156,157
Liquid phase reaction	Chemical vapor deposition	High crystallinity, uniform	Small-scale; substrate-dependent	Nano	Wire	158,159
	Sol-gel method	Low-cost, facile	Shrinkage upon drying	Nano	Spherical	160,161
Solution combustion	Hydrothermal method	Low-cost, high crystallinity	Conditional reaction	Nano	Snowflake	162,163
	Seeded growth	Controllable crystal growth	Pressure requirement	Nano	Star	164,165
	Solution combustion	Low-cost, time-saving, controllable composition	Small-scale; uneven grain size	Micro/nano	Irregular	166,167

Micro/nano-engineering, offering new degrees of freedom in the design and manufacturing of VO₂-based thermochromic materials, also presents challenges regarding manufacturing complexity and cost control. It is suggested that future efforts should be directed towards streamlining the manufacturing process and reducing costs, without compromising or enhancing material performance.



To develop high-performance and cost-effective VO₂-based smart windows, researchers must gain a deep understanding and precise control of the doping mechanisms, utilize micro/nano-engineering techniques to optimize optical properties, and balance *T_c* with optical characteristics. By employing precise doping strategies and micro/nano-engineering techniques, *T_{lum}* and ΔT_{sol} can be optimized. Additionally, simplifying the manufacturing process to reduce costs is essential to ensure the product's performance and economic viability in practical applications.

Methods

Preparation of VO₂ nanoparticles

High-quality VO₂ NPs with narrow distribution and uniform morphology are undoubtedly conducive to fabricate ideal thermochromic films. Recently, several methods have been reported to prepare definitive VO₂ particles, as shown in Table 3. For instance, solid-phase reaction methods offer low-cost and large-scale production but may involve toxic reactants and impurities, while gas-phase reaction methods provide morphological control but are often constrained by conditional reactions and equipment complexity.

CVD and PVD methods are typically constrained by expensive and intricate equipment, often resulting in low yield. The hydrothermal method usually necessitates precise control over temperature and atmosphere, while ball-milling and thermal reduction methods are prone to introducing impurities. In contrast, the pyrolysis process offers advantages such as mild reaction conditions, controllable product composition, and minimal impurity introduction, making it conducive to large-scale production. Recent advancements, such as the combination of solvent-thermal and pyrolysis processes, have led to the synthesis of purer VO₂ powder with high crystallinity. Hua et al. employed a combination of solvent-thermal and pyrolysis processes to synthesize purer VO₂ powder under mild air conditions. Through manual grinding and etching processes, they obtained innovative VO₂(M) nanoparticles with high crystallinity⁵⁵. The equations for the aforementioned processes are as follows:



The preparation of VO₂ nanoparticles is a critical step in the development of VO₂-based thermochromic smart

windows. While various methods have been explored, each with its own set of advantages and limitations, the pyrolysis process stands out for its mild reaction conditions and minimal impurity introduction, which are particularly beneficial for large-scale production.

Fabrication of VO₂-based thermochromic films

Thus far, a multitude of methods have been devised to produce high-quality VO₂ films with outstanding thermochromic properties^{78–80}. These methods can be broadly categorized into chemical and physical techniques. Among them, CVD stands out as a commonly employed fabrication method for VO₂ thin films, owing to its merits of high deposition rate, uniform structure, excellent adhesion, and scalability. In the CVD process, a precursor containing metal ions is dissolved in a solvent and then transported by an inert carrier gas to the deposition reactor, where the chemical reaction occurs, as illustrated in Fig. 6a. For instance, electric-field assisted chemical vapor deposition (EACVD)⁷⁸ and low temperature chemical vapor deposition (LTCVD)⁸⁰ have been developed to enhance thermochromic properties and facilitate low-cost production.

Guo et al. prepared thermochromic VO₂ thin films (ΔT_{sol} 9.7% and T_{lum} 52.3%) by LTCVD at a lower T_c . This reduction in T_c was attributed to the combined effects of strain and the presence of oxygen vacancies in the films during annealing. However, there has been limited emphasis on comparatively large-scale production, and the precursors commonly used as vanadium sources in the CVD process are typically toxic and environmentally unfriendly, such as VCl₄⁸¹, VO(acac)₂⁸², VO(OC₃H₇)₃⁸³, etc. PVD is an extensively researched technique for depositing high-quality VO₂ thin films, particularly for applications like smart windows, due to its ability to produce highly homogeneous products, good repeatability, and potential for large-scale production. Examples include magnetron sputtering (MS)^{63,84} and pulsed laser deposition (PLD)⁸⁵, etc.

As illustrated in Fig. 6b, MS is a vacuum process used to deposit thin films on substrates by applying a high voltage across a low-pressure gas (usually argon) to create a “plasma”. Energized plasma ions strike the target and cause atoms from that target to be ejected with enough energy to travel to and bond with the substrate. While PVD methods offer superior quality and crystallinity in the fabrication of VO₂ thin films compared to other techniques, the complexity and expense of the equipment, along with high maintenance costs, severely limit their practical widespread application in smart windows⁸⁶. Furthermore, persisting issues include poor antioxidizability and weatherability⁸⁷. Hence, there is a demand for facile, low-cost, eco-friendly, scalable, and high-quality fabrication methods for VO₂-based thin films.


Electrospinning is a technique wherein a high electric field is directly applied to obtain fibers with diameters ranging from nanometers to micrometers⁸⁸. This process typically comprises four components: a high-voltage power supply, a syringe pump, a spinneret, and a collector, as illustrated in Fig. 6c⁸⁹. It is commonly employed in the fabrication of organic-inorganic film materials⁹⁰.

In comparison with existing methods, the electrospinning technique is straightforward, mature, versatile, economical, and efficient for preparing continuous nanofibers with high porosity. These fibers have been proven to possess exceptional optical properties suitable for radiative-cooling applications⁹¹. Li et al. utilized electrospinning to prepare W-doped VO₂/PVP composite fiber mats and identified two modes of the multiple scattering-absorbing process when light was absorbed by the fiber mats⁹². Due to the constitution of the fibers in the electrospun film, internal scattering is one of the reasons of low T_{lum} for electrospun thermochromic films. Therefore, proper T_{lum} -enhanced techniques are necessary. Lu et al. firstly fabricated PMMA-VO₂ transparent composite smart film (ΔT_{sol} 6.9% and T_{lum} 21%) with antioxidizability and super-hydrophobicity by electrospinning method, attributed to the gathered VO₂ embedded in the fiber and aligned along the fiber axis. Subsequent heat treatment process significantly enhanced its T_{lum} ⁸⁷.

Spin coating is a solution-based technique employed to deposit uniform thin films onto flat substrates. Typically, a small amount of coating material is applied to the center of the substrate, which is then rotated at high speed to spread the coating material through centrifugal force, as illustrated in Fig. 6d. Zhao et al. synthesized W-VO₂ thermochromic films (ΔT_{sol} 8.8% and T_{lum} 41.5%) on an amorphous glass substrate using a simple spin coating method, which is economical, straightforward, and practical. However, high-speed spinning becomes challenging as the substrate size increases, making film thinning difficult. Additionally, the material efficiency of spin coating is relatively low⁹³, which limits its application for large-scale production.

In film casting, a solution (referred to as “dope”) of a polymer in a solvent is prepared and then applied to a moving substrate belt with a smooth surface⁹⁴. The wet film levels on the belt before entering the drying zone, where the solvent is completely removed to form a solid layer. Subsequently, the dry film is peeled from the belt, which then cycles back to the coating station, as depicted in Fig. 6e.

Gao et al. were the first to prepare transparent and flexible VSQ composite foils using an all-solution casting process. These foils exhibited a UV-shielding property and excellent thermochromic properties (ΔT_{sol} 15.5% and T_{lum} 41%)⁹⁵. In addition to wet coating with a solution, hot-melt casting is

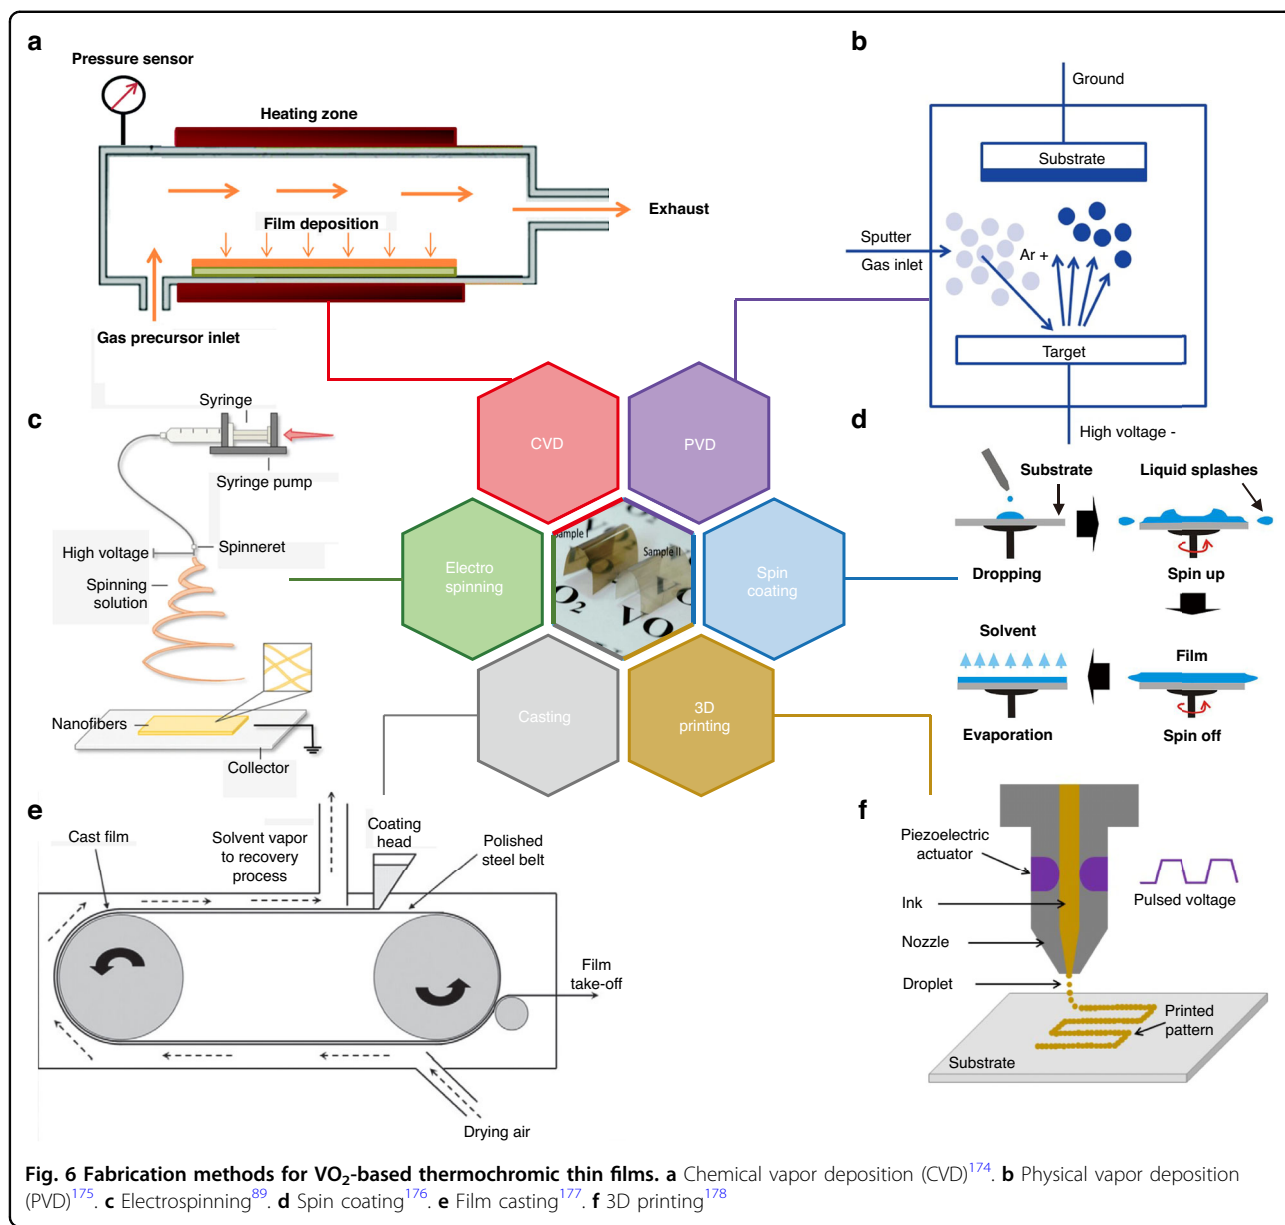

another method utilized for film deposition. A formulation is cast into a film from either hot melt or solution without solvent. The casting process offers several advantages over other methods, including simplicity of mold, low cost, absence of residual stresses, and suitability for low-production applications. It provides superior optical characteristics with a high degree of flatness compared to flat-sheet extrusion. However, casted parts may exhibit significant shrinkage post-solidification.

3D printing, or additive manufacturing, is a process for creating three-dimensional solid objects from a digital file. It encompasses various techniques, such as direct ink writing (DIW), stereolithography (SLA), selective laser melting (SLM)/selective laser sintering (SLS), and inject printing,

among others. For example, one method involves selectively depositing droplets of printing materials to form the desired structure, utilizing an X-Y-Z three-axis motion platform, spray heads, and auxiliary curing devices^{96,97}, as depicted in Fig. 6f. During the printing process, the fluid is ejected from the nozzle. With the movement of the platform, the ejected droplets are accurately deposited on the printing platform, and then solidified and formed at room temperature and atmospheric pressure. This method is low-cost, fast, efficient, flexible and suitable for the roll-to-roll process of complex structures, especially for materials that are difficult to form continuous wires.

However, there are limitations in printing height and mechanical properties of products. Ji et al. reported a

straightforward large-scale fabrication of uniform VO₂ thermochromic films using the inkjet printing technique (ΔT_{sol} : 32.4%). Large area VO₂ films (560 cm²) could be obtained with excellent uniformity, with the difference in NIR transmittance of regions on the film being within 0.3%⁹⁸.

The fabrication of VO₂-based thermochromic films is a multifaceted process with a variety of techniques offering different benefits. CVD and PVD are recognized for their high-quality film production, yet their scalability and environmental impact present challenges. Electrospinning and spin coating provide more accessible and cost-effective alternatives, with the potential for large-scale production.

Despite the success of existing fabrication methods at the laboratory scale, challenges remain in scaling up production and ensuring environmental adaptability. Future research is recommended to focus on the development of scalable, environmentally friendly, and cost-effective fabrication techniques. Additionally, it should explore new materials and structural designs to further enhance the performance and stability of VO₂-based thermochromic films.

Other chromogenic materials

Despite significant efforts to enhance the optical responses of VO₂-based thermochromic films, the overall T_{lum} and ΔT_{sol} remain constrained due to the intrinsic absorption of VO₂. In the following section, we delve into a variety of alternative chromogenic materials that exhibit significant optical property changes, which are extensively utilized to modulate solar radiation. The potential for synergistic integration of these materials with VO₂ will be explored, with the aim of further refining spectral transmittance. Prominent among these are electro-, gaso-, mechano-, photochromic materials, each of which is activated by specific stimuli such as an electric field, gas exchange, mechanical stress, and light exposure. These smart chromogenic technologies each bring a unique set of advantages and challenges, and they are the focus of continuous innovation to improve their functionality and efficiency. The characteristics of various chromogenic materials are summarized in Table 4.

Electrochromic (EC) materials could reversibly change the optical properties under the influence of electric field, including inorganic metal oxides (TiO₂⁹⁹, etc.), organic polymers (propylenedioxythiophene¹⁰⁰, etc.), inorganic-organic hybrids: coordination complex¹⁰¹, prussian blue¹⁰², liquid crystal (Fig. 7a)⁸, etc. EC applications are composed of EC material, electrolyte, ion storage layer, etc. and sandwiched by two transparent conductive electrodes¹⁰³. The advantages of electrochromic (EC) materials include easy operation through a control system and integration into the Internet of Things (IoT).

However, challenges such as poor UV durability (especially for polymer-based EC materials), coloration efficiency, cycling stability, and indoor-use restrictions remain to be addressed in the future. Sang et al. proposed a smart window (ΔT_{sol} : 32.4% and T_{lum} : 0.4–40%) with a dual-band modulation function based on a simple three-layer structure of liquid crystal, VO₂ and Al-doped ZnO, which can modulate the visible light actively by an external electric field and NIR light passively by temperature¹⁰⁴.

Gasochromic (GC) materials are a type of thermochromics displaying a color change responding to a chemical change or reaction^{105,106}. WO₃ is a well-known example of GC materials. In a double-glazed structure, the internal surfaces coated with a WO₃ film exhibit reversible light transmittance switching when alternately exposed to diluted hydrogen and oxygen gases, as illustrated in Fig. 7b. One advantage of GC materials, such as WO₃, is that the depth and switching speed of color change can be controlled by adjusting the film thickness and the concentration of hydrogen and oxygen gases. Due to their straightforward and cost-effective layer configuration, as well as high light transmittance, WO₃-based GC devices have garnered significant attention since the beginning of the 21st century^{107,108}. However, a major limitation of these devices is the requirement for a system to provide hydrogen and oxygen gases.

Mechanochromic (MC) materials respond to mechanical stimuli which can deform and reconstruct the surface morphologies or internal structures with a change of their optical properties¹⁰⁹, like polyvinyl alcohol (PVA)/PDMS¹¹⁰, diarylbibenzofuranone (DABBF) (Fig. 7c), etc. The MC applications are facile, eco-friendly, and responsive. The main obstacles to their commercialization include the significant applied biaxial strain and area expansion resulting from stretching, as well as the improvement of the fatigue life of cracks under high strength mechanical loading cycles without incurring catastrophic structural damage^{111,112}. Ke et al. presented a bio-inspired thermo-mechanochromic dual-mode VO₂/PVA/PDMS window (ΔT_{sol} : 11.5% and T_{lum} : 17–60%), to respectively control the scattering for privacy and the absorbance for energy-efficiency, which are attributed to the controllable broadband diffraction via the dynamic wrinkles and VO₂ NPs based on LSPR¹¹³.

Photochromic (PC) materials undergo reversible transformation when exposed to specific wavelengths of light, which could be roughly divided into organic and inorganic PC materials. Common examples include fulgide¹¹⁴, diarylethene¹¹⁵, spiropyran¹¹⁶ (as depicted in Fig. 7d), TiO₂¹¹⁷, etc. Compared to inorganic counterparts, organic PC materials possess great advantage in structural diversity, photochromic reversibility, and processibility^{118,119}. However, simply removing the UV is not

Table 4 Characteristics of different chromogenic materials

Chromogenic material type	Characteristics	Fabrication methods	Cost	Pros	Cons	Ref.
Electrochromic (TiO ₂ , etc.)	Reversibly changing optical properties under electric field	Electrochemical deposition, solution immersion, etc.	Variable	Easy operation, IoT integration, adjustable color, excellent performance in reversible color change	Poor UV durability for polymer-based EC materials, low coloration efficiency, cycling stability issues, indoor-use restriction	101
Gasochromic (WO ₃ , etc.)	Displaying color change in response to chemical change or reaction	Sol-gel method, chemical vapor deposition, etc.	Low	Depth and switching speed controllable by film thickness and gas concentration, easy configuration and cost efficiency, high light transmittance	Requiring hydrogen and oxygen providing system	105,106
Mechanochromic (PVA, PDMS, DABBF, etc.)	Responding to mechanical stimuli and changes in surface morphologies and internal structures	Mechanical processing, embossing, etc.	Low to moderate	Simple, eco-friendly, responsive	Biaxial strain and area expansion from stretching, short fatigue life of cracks under high strength mechanical loading cycles	109
Photochromic (fulgide, diarylethene, spiropyran, TiO ₂ , etc.)	Reversible transformation when exposed to specific wavelengths of light	Solution processing, electrochemical polymerization, etc.	Variable	Structural diversity, photochromic reversibility, processibility	Ineffective initial color restoration under UV illumination, limited photochromic library	121
Thermochromic (VO ₂ , perovskites, hydrogels, etc.)	Changing optical properties based on temperature	physical vapor deposition, chemical vapor deposition, sol-gel method, etc.	Low	Suitable for passive light modulation	Requirements for specific spectral characteristics	48

sufficient to restore most organic PC materials to their initial color (except for naphthopyran)^{119,120}, and more basic research is needed to enrich the library of photochromism. Sang et al. fabricated a novel VO₂/spiropyran composite film (ΔT_{sol} 23.6% and T_{lum} 31.55–48.6%), which could simultaneously modulate UV, visible, and NIR light with obvious color change from yellow to pink reversibly¹²¹.


Thermochromic materials enable a change in optical properties based on the temperature¹²², which is suitable for passive light modulation. In addition to VO₂⁴⁸, perovskites (Fig. 7e)¹²³ and hydrogels⁵¹ are also very representative. They have their own spectral characteristics towards application scenarios in demand.

The exploration of alternative chromogenic materials offers a promising avenue for addressing the limitations of VO₂-based thermochromic coatings. These aforementioned materials demonstrate significant changes in optical properties and are widely utilized in solar radiation modulation. Integrating these materials with VO₂ has the potential to further enhance functionality in

smart windows. Each of these chromogenic technologies presents unique advantages and challenges, spurring continuous innovation to enhance their efficiency and performance. Through synergistic integration, these materials can enable smart windows to achieve improved optical responses and multifunctionality, thus facilitating their broader adoption in energy-efficient building applications.

Conclusion and outlook

Here, we present a comprehensive review on the VO₂-based thermochromic coatings for smart windows. With the inspiring MIT transition, VO₂ serves as a promising material for spectral transmittance modulation. Given the limitations of pristine VO₂, such as its high transition temperature, low luminous transmittance, and weak solar-energy modulation ability, a variety of research approaches have been proposed, spanning from the crystal level to the structural level, including elemental doping and micro-nano structural engineering. Based on the latest researches, we discuss the principles and results

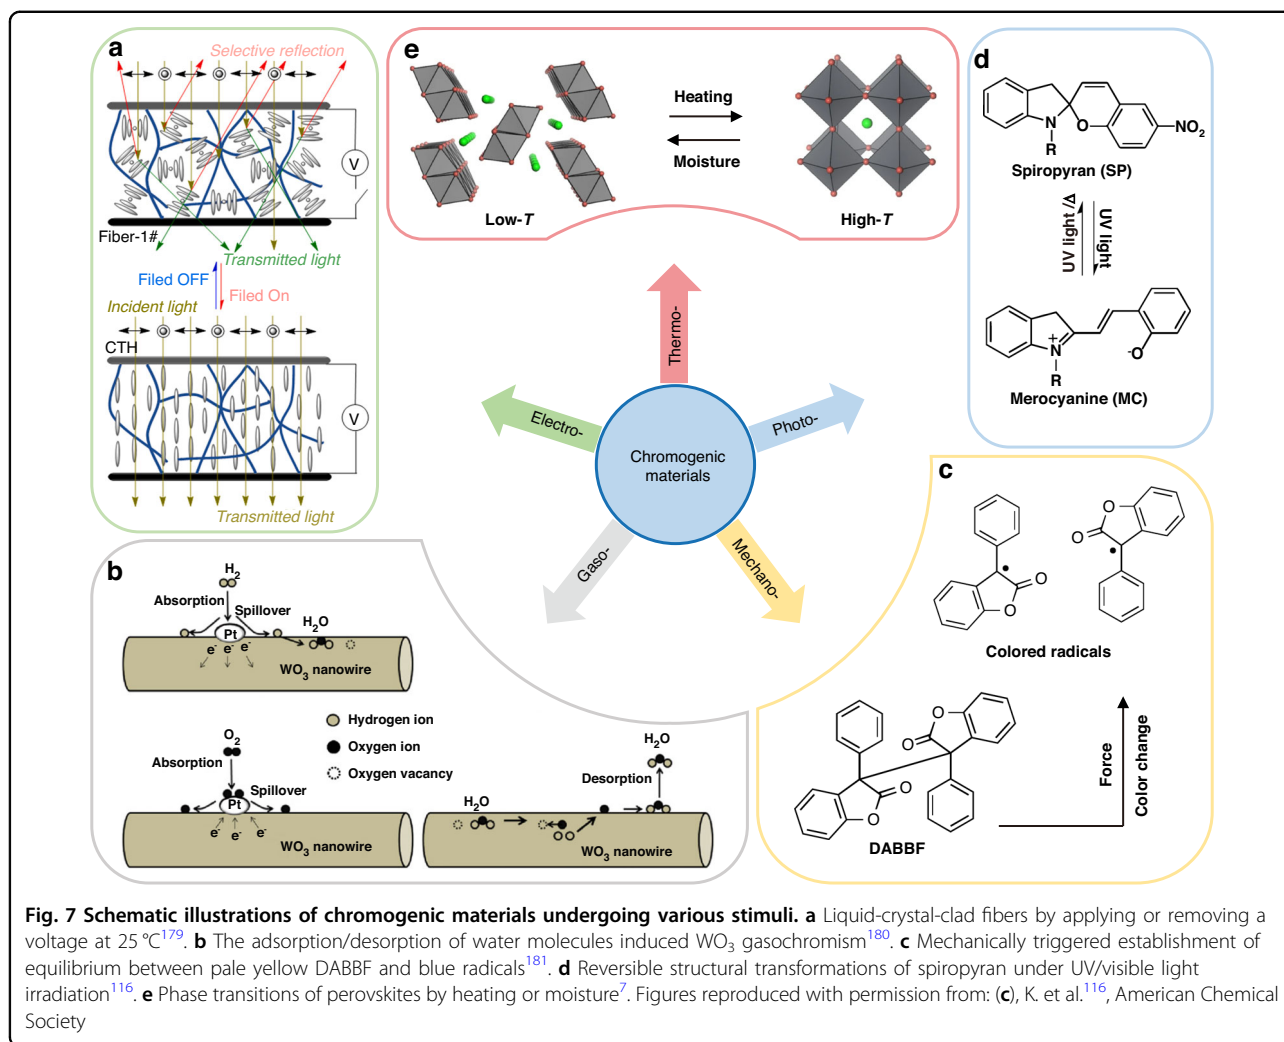

of micro/nano-engineering in detail by categories including hybridization, core-shell structures and multi-layer film design. Moreover, we summarize the fabrication methods of VO₂ NPs and VO₂-based thermochromic films. We also provide discussions on other chromogenic materials, which can be integrated for thermochromic smart windows as an alternative strategy to surpass the intrinsic limitation of VO₂. Besides the above conclusions and summarizations, outlooks and prospects are discussed as follows, which aim to inspire more innovative progress and accelerate the development of this research field from the lab to the industry.

VO₂-based thermochromic smart windows represent an important technology for increasing indoor comfort and reducing energy consumption in the building. Hence, this hotspot is promising and competitive. Some problems still need to be addressed to further widen their practical applications.

- a. Idealizing the optical responses including T_{lum} , ΔT_{sol} and ΔT_{NIR} . To facilitate the commercialization of

VO₂-based radiative cooling coatings, ideally ΔT_{sol} and ΔT_{NIR} should be respectively increased to 57% and 100% with high T_{lum} . This is where researchers had made efforts upon micro/nano-engineering. Further investigations on micro/nano-engineering should be revealed with more complex core-shell micro/nanostructures, higher order optical resonances and combining with other chromogenic materials discussed in Other Chromogenic Materials.

- b. Continuous and various color changes. Color preference is tightly related to local customs with high versatility. For instance, a colorless coating or coloration with light blue/green is acceptable in China¹²⁴. While gold or violet is more attractive in some areas of Southeastern Asia or Arabia¹²⁵. More sophisticated core-shell or multilayer structure design can help us to achieve this goal.
- c. Stability and lifetime. Vanadium is multivalent transition element, which reveals +3, +4, +5, and mixed valences. VO₂(M) tends to be oxidized to

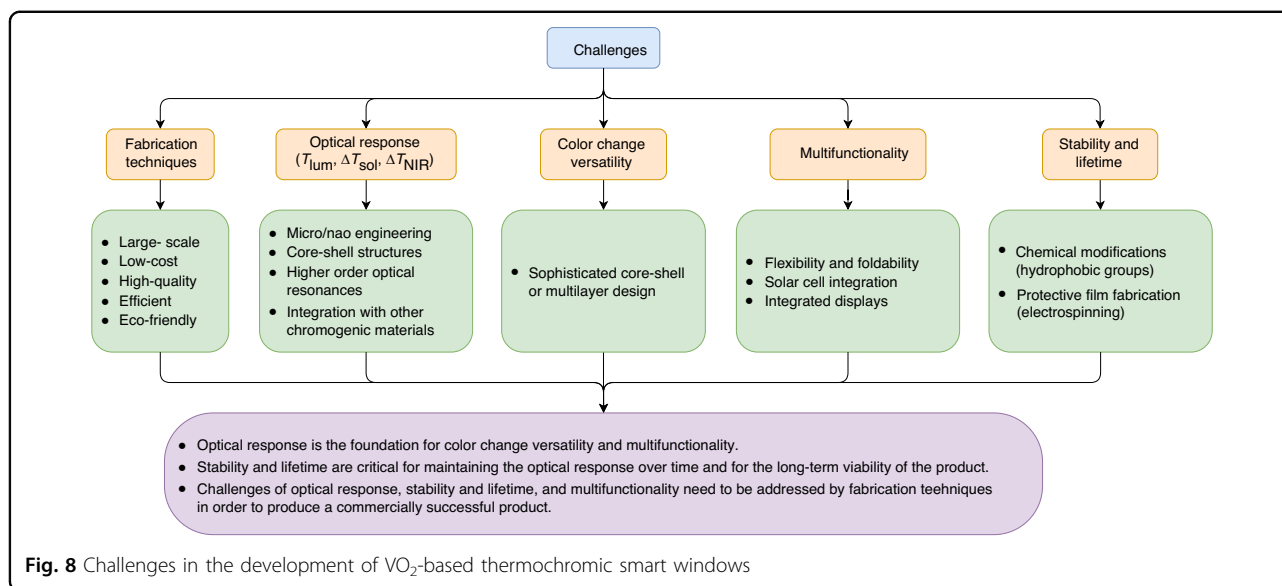


Fig. 8 Challenges in the development of VO₂-based thermochromic smart windows

VO₂O₅ or their hydroxides, especially in a humid environment. This instability leads to low lifetime in practical applications. Therefore, the antioxidizability and hydrophobicity of VO₂-based thermochromic films are worthy of our attention. VO₂-based core-shell micro/nano-structure design might already enhance the antioxidizability to some extent, while affect the luminous transmittance of thermochromic films. Introducing hydrophobic groups on the surface of films to trap water molecules by grafting, etc. chemical modification means¹²⁶ and protective film fabrication methods, i.e., electrospinning¹²⁷ would be bright solutions.

- d. Superior fabrication techniques for VO₂-based thermochromic coatings need to be of large-scale, low-cost, high-quality, high efficiency, and eco-friendly, etc.
- e. Broadening the multifunctionality of smart windows, e.g., introducing flexibility and foldability, integration of solar cells for electricity generation, integrated display for interactivity, etc.
- f. Exploiting VO₂ in advanced applications for radiative cooling¹²⁸, warming¹²⁹, and camouflage^{130,131}: The potential of VO₂ extends beyond smart windows into the realms of radiative cooling, warming, and camouflage technologies. The thermochromic nature of VO₂ allows for the development of coatings that can dynamically regulate heat exchange with the environment, making them ideal candidates for applications where temperature control and thermal management are critical. For radiative cooling, VO₂ coatings could automatically adjust their

thermal emissivity to reflect more solar energy and emit more thermal radiation, thereby reducing the need for artificial cooling systems. In the context of warming, VO₂ could be engineered to absorb more solar energy while reducing thermal radiation loss, providing an energy-efficient approach to heating. Moreover, in the field of camouflage, VO₂-based coatings could change their thermal signature in response to environmental conditions, making objects less detectable by infrared sensors. The challenge lies in tailoring the phase transition temperature of VO₂ to operate effectively under varying conditions and integrating these coatings into practical systems while maintaining their optical and thermal performance. Future research should focus on the scalable production of VO₂ coatings with tailored properties, their integration with other advanced materials for enhanced performance, and the development of dynamic control systems for responsive thermal management.

To further elucidate the challenges and corresponding solution paths in the development of VO₂-based thermochromic smart windows, we have prepared a summary, as depicted in Fig. 8. This figure provides readers with a clear visualization of the strategies proposed to address the challenges identified in this review, facilitating a deeper understanding of the research landscape and potential avenues for future exploration.

Acknowledgements

C.J. and L.H. thanks Chunlei Su for checking the fabrication methods presented in the manuscript and Yang Fu and Shixuan Zhao for their guidance on core-

shell structure simulations. D.L. thanks Tao Wang, Ying Liu, and Yanbo Fang for their proof reading of the manuscript.

Author details

¹Department of Materials Science and Engineering, Centre for Functional Photonics, and Hong Kong Branch of National Precious Metals Material Engineering Research Centre, City University of Hong Kong, Kowloon, Hong Kong 999077, China. ²Department of Refrigeration and Cryogenics Engineering, Hefei University of Technology, 193 Tunxi Road, Hefei 230009, China. ³Department of Architecture and Civil Engineering, City University of Hong Kong, Kowloon, Hong Kong 999077, China

Author contributions

C.J. and L.H. wrote the manuscript. D.L. supervised the project and revised the manuscript. All authors participated in the discussions.

Funding

We acknowledge the financial support by the City University of Hong Kong through an ARG project (9667246), the Innovation and Technology Commission of Hong Kong through a Mainland-Hong Kong Joint Funding Scheme grant (MHP/162/22), and the Research Grants Council of Hong Kong through a Collaborative Research Project Grant (C5050-22GF).

Conflict of interest

The authors declare no competing interests.

Received: 14 November 2023 Revised: 30 June 2024 Accepted: 31 July 2024

Published online: 18 September 2024

References

- Ramesh, T., Prakash, R. & Shukla, K. K. Life cycle energy analysis of buildings: an overview. *Energy Build* **42**, 1592–1600 (2010).
- Baetens, R., Jelle, B. P. & Gustavsen, A. Properties, requirements and possibilities of smart windows for dynamic daylight and solar energy control in buildings: A state-of-the-art review. *Sol. Energy Mater. Sol. Cells* **94**, 87–105 (2010).
- Park, H. K. & Kim, H. Acoustic insulation performance of improved airtight windows. *Constr. Build. Mater.* **93**, 542–550 (2015).
- Tuchinda, C., Srivannaboon, S. & Lim, H. W. Photoprotection by window glass, automobile glass, and sunglasses. *J. Am. Acad. Dermatol.* **54**, 845–854 (2006).
- Edlich, R. et al. Use of UV-protective windows and window films to aid in the prevention of skin cancer. *J. Long-Term Eff. Med. Implants* **14**, 15 (2004).
- Chabane, I. J. & Bensalem, R. In The 23rd Conference on Passive and Low Energy Architecture. (Geneva, Switzerland, 2006).
- Lin, J. et al. Thermochromic halide perovskite solar cells. *Nat. Mater.* **17**, 261–267 (2018).
- Heo, J., Huh, J.-W. & Yoon, T.-H. Fast-switching initially-transparent liquid crystal light shutter with crossed patterned electrodes. *AIP Adv.* **5**, 047118 (2015).
- Kwon, J. et al. In Emerging Liquid Crystal Technologies XV. (SPIE, 2020).
- Lei, D. Y. et al. Optically-triggered nanoscale memory effect in a hybrid plasmonic-phase changing nanostructure. *ACS Photonics* **2**, 1306–1313 (2015).
- Liang, J., Hou, L. & Li, J. Frequency tunable perfect absorber in visible and near-infrared regimes based on VO₂ phase transition using planar layered thin films. *JOSA B* **33**, 1075–1080 (2016).
- Liang, J., Zhao, Y., Zhu, K., Guo, J. & Zhou, L. Synthesis and room temperature NO₂ gas sensitivity of vanadium dioxide nanowire structures by chemical vapor deposition. *Thin Solid Films* **669**, 537–543 (2019).
- Yang, Z., Ko, C. & Ramanathan, S. Oxide electronics utilizing ultrafast metal-insulator transitions. *Annu. Rev. Mater. Res.* **41**, 337–367 (2011).
- Goodenough, J. B. The two components of the crystallographic transition in VO₂. *J. Solid State Chem.* **3**, 490–500 (1971).
- Yu, F.-y et al. A terahertz tunable metamaterial reflective polarization converter based on vanadium oxide film. *Plasmonics* **17**, 823–829 (2022).
- Yu, F.-y, Zhu, J.-b. & Shen, X.-b Tunable and reflective polarization converter based on single-layer vanadium dioxide-integrated metasurface in terahertz region. *Opt. Mater.* **123**, 111745 (2022).
- Liu, M. et al. Dual-phase transformation: Spontaneous self-template surface-patterning strategy for ultra-transparent VO₂ solar modulating coatings. *ACS Nano* **11**, 407–415 (2017).
- Cui, Y. et al. Thermochromic VO₂ for energy-efficient smart windows. *Joule* **2**, 1707–1746 (2018).
- Son, S. B., Youn, J. W., Kim, K.-S. & Kim, D. U. Optical properties of periodic micropatterned VO₂ thermochromic films prepared by thermal and intense pulsed light sintering. *Mater. Des.* **182**, 107970 (2019).
- Liang, J., Song, X., Li, J., Lan, K. & Li, P. A visible-near infrared wavelength-tunable metamaterial absorber based on the structure of Au triangle arrays embedded in VO₂ thin film. *J. Alloy. Compd.* **708**, 999–1007 (2017).
- Wyszecki, G. & Stiles, W. S. Color Science. 982 (John Wiley & Sons, New York, 1982).
- Jelle, B. P. Solar radiation glazing factors for window panes, glass structures and electrochromic windows in buildings—Measurement and calculation. *Sol. Energy Mater. Sol. Cells* **116**, 291–323 (2013).
- Wyszecki, G. & Stiles, W. S. Color science: concepts and methods, quantitative data and formulae Vol. 40. (John Wiley & Sons, 2000)
- ASTM, Standard Tables for Reference Solar Spectral Irradiances: Direct Normal and Hemispherical on 37° Tilted Surface. (ASTM G173-03, <https://www.astm.org/g0173-03r20.html>. Accessed 2020).
- ISO 9050. Glass in building-determination of light transmittance, solar direct transmittance, total solar energy transmittance, ultraviolet transmittance and related glazing factors. (ISO, Geneva, Switzerland, 2003(E)).
- ISO 10526. CIE standard illuminants for calorimetry. (ISO, Geneva, Switzerland, 1999(E)).
- Yuan, X., Zhang, W. & Zhang, P. Hole-lattice coupling and photoinduced insulator-metal transition in VO₂. *Phys. Rev. B* **88**, 035119 (2013).
- Yuan, X., Zhang, Y., Abtey, T. A., Zhang, P. & Zhang, W. VO₂: Orbital competition, magnetism, and phase stability. *Phys. Rev. B* **86**, 235103 (2012).
- Cui, Y., Shi, S., Chen, L., Luo, H. & Gao, Y. Hydrogen-doping induced reduction in the phase transition temperature of VO₂: a first-principles study. *Phys. Chem. Chem. Phys.* **17**, 20998–21004 (2015).
- Fan, L. et al. A facile strategy to realize rapid and heavily hydrogen-doped VO₂ and study of hydrogen ion diffusion behavior. *J. Phys. Chem. C* **126**, 5004–5013 (2022).
- Cui, Y., Wang, Y., Liu, B., Luo, H. & Gao, Y. First-principles study on the phase transition temperature of X-doped (X= Li, Na or K) VO₂. *RSC Adv.* **6**, 64394–64399 (2016).
- Chen, Y. et al. Electric-field control of Li-doping induced phase transition in VO₂ film with crystal facet-dependence. *Nano Energy* **51**, 300–307 (2018).
- Top, I. et al. The effect of alkali metal (Na, K) doping on thermochromic properties of VO₂ films. *MRS Adv.* **3**, 1863–1869 (2018).
- Zhou, Q. et al. Boron doped M-phase VO₂ nanoparticles with low metal-insulator phase transition temperature for smart windows. *Ceram. Int.* **46**, 4786–4794 (2020).
- Hajlaoui, T. et al. Metal-insulator transition temperature of boron-doped VO₂ thin films grown by reactive pulsed laser deposition. *Scr. Materialia* **177**, 32–37 (2020).
- Hu, L. et al. Porous W-doped VO₂ films with simultaneously enhanced visible transparency and thermochromic properties. *J. Sol.-Gel Sci. Technol.* **77**, 85–93 (2016).
- Bleu, Y. et al. Towards Room Temperature Phase Transition of W-Doped VO₂ Thin Films Deposited by Pulsed Laser Deposition: Thermochromic, Surface, and Structural Analysis. *Materials* **16**, 461 (2023).
- Mai, L., Hu, B., Hu, T., Chen, W. & Gu, E. Electrical property of Mo-doped VO₂ nanowire array film by melting-quenching sol-gel method. *J. Phys. Chem. B* **110**, 19083–19086 (2006).
- Piccirillo, C., Binions, R. & Parkin, I. P. Nb-Doped VO₂ Thin Films Prepared by Aerosol-Assisted Chemical Vapour Deposition. *Eur. J. Inorg. Chem.* **25**, 4050–4055 (2007).
- Cui, Y., Cao, C., Chen, Z., Luo, H. & Gao, Y. Atomic and electronic structures of thermochromic VO₂ with Sb-doping. *Computational Mater. Sci.* **130**, 103–108 (2017).
- Zhang, J., He, H., Xie, Y. & Pan, B. Giant reduction of the phase transition temperature for beryllium doped VO₂. *Phys. Chem. Chem. Phys.* **15**, 4687–4690 (2013).

42. Shao, Z. et al. Tri-band electrochromic smart window for energy savings in buildings. *Nat. Sustain.* **7**, 796–803 (2024).
43. Appavoo, K. et al. Role of defects in the phase transition of VO₂ nanoparticles probed by plasmon resonance spectroscopy. *Nano Lett.* **12**, 780–786 (2012).
44. Lazarovits, B., Kim, K., Haule, K. & Kotliar, G. Effects of strain on the electronic structure of VO₂. *Phys. Rev. B* **81**, 115117 (2010).
45. Chen, Z., Cao, C., Chen, S., Luo, H. & Gao, Y. Crystallised mesoporous TiO₂ (A)-VO₂ (M/R) nanocomposite films with self-cleaning and excellent thermochromic properties. *J. Mater. Chem. A* **2**, 11874–11884 (2014).
46. Du, J. et al. Formation and metal-to-insulator transition properties of VO₂-ZrV₂O₇ composite films by polymer-assisted deposition. *Sol. Energy Mater. Sol. Cells* **95**, 1604–1609 (2011).
47. Li, S.-Y., Niklasson, G. A. & Granqvist, C.-G. Nanothermochromics: Calculations for VO₂ nanoparticles in dielectric hosts show much improved luminous transmittance and solar energy transmittance modulation. *J. Appl. Phys.* **108**, 063525 (2010).
48. Liang, J., Wang, S., Lei, D., Wang, Z. & Li, X. Enhanced visible and tunable infrared transmittance of W-doped VO₂/SiO₂/PVP composite films for smart windows. *Optical Mater.* **121**, 111485 (2021).
49. Hao, Q. et al. VO₂/TiN plasmonic thermochromic smart coatings for room-temperature applications. *Adv. Mater.* **30**, 1705421 (2018).
50. Cao, Z. et al. Tunable simultaneously visible-light and near-infrared transmittance for VO₂/SiO₂ composite films to enhance thermochromic properties. *Mater. Lett.* **209**, 609–612 (2017).
51. He, Q. et al. PAM-PNIPAM/W-doped VO₂ thermochromic hydrogel film with high solar modulation capability for smart windows deployment. *Optical Mater.* **97**, 109367 (2019).
52. Liang, J. et al. Periodic Arrays of 3D AuNP-Capped VO₂ Shells and Their Temperature-Tunable SERS Performance. *Adv. Optical Mater.* **10**, 2102615 (2022).
53. Xie, Y. et al. Influence of shell materials on the optical performance of VO₂ core-shell nanoparticle-based thermochromic films. *Mater. Today Nano* **13**, 100102 (2021).
54. Pi, J. et al. Superhydrophobic and thermochromic VO₂-Based composite coatings for energy-saving smart windows. *Compos. Commun.* **32**, 101167 (2022).
55. Zhou, Y. et al. Surface plasmon resonance induced excellent solar control for VO₂@SiO₂ nanorods-based thermochromic foils. *Nanoscale* **5**, 9208–9213 (2013).
56. Lu, X. et al. A novel method to modify the color of VO₂-based thermochromic smart films by solution-processed VO₂@SiO₂@Au core-shell nanoparticles. *RSC Adv.* **6**, 47249–47257 (2016).
57. Yao, L. et al. Three-layered hollow nanospheres based coatings with ultra-high-performance of energy-saving, antireflection, and self-cleaning for smart windows. *Small* **14**, 1801661 (2018).
58. Lee, M. et al. Photonic structures in radiative cooling. *Light Sci. Appl.* **12**, 134 (2023).
59. Parker, J. Raman scattering from VO₂ single crystals: A study of the effects of surface oxidation. *Phys. Rev. B* **42**, 3164 (1990).
60. Zhan, Y. et al. The growth mechanism of VO₂ multilayer thin films with high thermochromic performance prepared by RTA in air. *Surf. Interfaces* **9**, 173–181 (2017).
61. Liu, H. et al. SnO₂/VO₂/SnO₂ tri-layer thermochromic films with high luminous transmittance, remarkable solar modulation ability and excellent hydrophobicity grown on glass substrates. *Infrared Phys. Technol.* **113**, 103648 (2021).
62. Ji, Y., Mattsson, A., Niklasson, G. A., Granqvist, C. G. & Österlund, L. Synergistic TiO₂/VO₂ window coating with thermochromism, enhanced luminous transmittance, and photocatalytic activity. *Joule* **3**, 2457–2471 (2019).
63. Zheng, J., Bao, S. & Jin, P. TiO₂ (R)/VO₂ (M)/TiO₂ (A) multilayer film as smart window: Combination of energy-saving, antifogging and self-cleaning functions. *Nano Energy* **11**, 136–145 (2015).
64. Liu, C. et al. Index-tunable anti-reflection coatings: Maximizing solar modulation ability for vanadium dioxide-based smart thermochromic glazing. *J. Alloy. Compd.* **731**, 1197–1207 (2018).
65. Xu, F. et al. Highly enhanced thermochromic performance of VO₂ film using “movable” antireflective coatings. *ACS Appl. Mater. Interfaces* **11**, 4712–4718 (2019).
66. Li, J. et al. Ultrathin, soft, radiative cooling interfaces for advanced thermal management in skin electronics. *Sci. Adv.* **9**, eadg1837 (2023).
67. An, Y., Fu, Y., Dai, J.-G., Yin, X. & Lei, D. Switchable radiative cooling technologies for smart thermal management. *Cell Rep. Phys. Sci.* **3**, 101098 (2022).
68. Ma, X. et al. Fluorescence-Enabled Colored Bilayer Subambient Radiative Cooling Coatings. *Adv. Opt. Mater.* **11**, 2303296 (2024).
69. Fu, Y., An, Y., Xu, Y., Dai, J. G. & Lei, D. Polymer coating with gradient-dispersed dielectric nanoparticles for enhanced daytime radiative cooling. *EcoMat* **4**, e12169 (2022).
70. Wang, S. et al. Scalable thermochromic smart windows with passive radiative cooling regulation. *Science* **374**, 1501–1504 (2021).
71. Tang, K. et al. Temperature-adaptive radiative coating for all-season household thermal regulation. *Science* **374**, 1504–1509 (2021).
72. Lang, F., Wang, H., Zhang, S., Liu, J. & Yan, H. Review on variable emissivity materials and devices based on smart chromism. *Int. J. Thermophys.* **39**, 1–20 (2018).
73. Xue, X. et al. Creating an eco-friendly building coating with smart sub-ambient radiative cooling. *Adv. Mater.* **32**, 1906751 (2020).
74. Ma, X. et al. Effects of Stokes shift and Purcell enhancement on fluorescence-assisted radiative cooling. *J. Mater. Chem. A* **10**, 19635–19640 (2022).
75. Yang, N., Fu, Y., Xue, X., Lei, D. & Dai, J. G. Geopolymer-based sub-ambient daytime radiative cooling coating. *EcoMat* **5**, e12284 (2023).
76. Zhu, Y. et al. Color-preserving passive radiative cooling for an actively temperature-regulated enclosure. *Light Sci. Appl.* **11**, 122 (2022).
77. Liu, Y. et al. Intelligent regulation of VO₂-PDMS-driven radiative cooling. *Appl. Phys. Lett.* **120**, 171704 (2022).
78. Warwick, M. E. & Binions, R. Electric field assisted aerosol assisted chemical vapor deposition of nanostructured metal oxide thin films. *Surf. Coat. Technol.* **230**, 28–32 (2013).
79. Ligmajer, F. et al. Epitaxial VO₂ nanostructures: a route to large-scale, switchable dielectric metasurfaces. *ACS Photonics* **5**, 2561–2567 (2018).
80. Guo, B. et al. Low temperature fabrication of thermochromic VO₂ thin films by low-pressure chemical vapor deposition. *RSC Adv.* **7**, 10798–10805 (2017).
81. Gaskell, J. M. et al. Optimised atmospheric pressure CVD of monoclinic VO₂ thin films with picosecond phase transition. *Surf. Coat. Technol.* **287**, 160–165 (2016).
82. Yin, H., Yu, K., Song, C., Wang, Z. & Zhu, Z. Low-temperature CVD synthesis of patterned core-shell VO₂@ZnO nanotetrapods and enhanced temperature-dependent field-emission properties. *Nanoscale* **6**, 11820–11827 (2014).
83. Vernardou, D., Louloudakis, D., Spanakis, E., Katsarakis, N. & Koudoumas, E. Thermochromic amorphous VO₂ coatings grown by APCVD using a single-precursor. *Sol. Energy Mater. Sol. Cells* **128**, 36–40 (2014).
84. Zhan, Y. et al. Enhanced thermal stability and thermochromic properties of VO_x-based thin films by room-temperature magnetron sputtering. *Sol. Energy Mater. Sol. Cells* **174**, 102–111 (2018).
85. Chang, T. et al. Flexible VO₂ thermochromic films with narrow hysteresis loops. *Sol. Energy Mater. Sol. Cells* **219**, 110799 (2021).
86. Manning, T. D., Parkin, I. P., Blackman, C. & Qureshi, U. APCVD of thermochromic vanadium dioxide thin films—solid solutions V_{2-x}M_xO₂ (M=Mo, Nb) or composites VO₂:SnO₂. *J. Mater. Chem.* **15**, 4560–4566 (2005).
87. Lu, Y. et al. Transparent optically vanadium dioxide thermochromic smart film fabricated via electrospinning technique. *Appl. Surf. Sci.* **425**, 233–240 (2017).
88. He, X. et al. Electrospun quantum dots/polymer composite porous fibers for turn-on fluorescent detection of lactate dehydrogenase. *J. Mater. Chem.* **22**, 18471–18478 (2012).
89. Tebyetekerwa, M., Xu, Z., Yang, S. & Ramakrishna, S. Electrospun nanofibers-based face masks, *Advanced Fiber. Materials* **2**, 161–166 (2020).
90. Tang, K. et al. Self-reduced VO/VO_x/carbon nanofiber composite as binder-free electrode for supercapacitors. *Electrochim. Acta* **209**, 709–718 (2016).
91. Shi, N. N. et al. Nanostructured fibers as a versatile photonic platform: radiative cooling and waveguiding through transverse Anderson localization. *Light Sci. Appl.* **7**, 37 (2018).
92. Li, S. et al. Functional fiber mats with tunable diffuse reflectance composed of electrospun VO₂/PVP composite fibers. *ACS Appl. Mater. Interfaces* **6**, 9–13 (2014).
93. Yilbas, B. S., Al-Sharafi, A. & Ali, H. In *Self-Cleaning of Surfaces and Water Droplet Mobility*. (eds Yilbas, B. S., Al-Sharafi, A., and Ali, H) 45-98 (Elsevier, 2019).
94. Narukawa Y. & Scriven, L. In *12th International Coating Science and Technology Symposium* (ISCST, Rochester, New York, USA, 2004).

95. Gao, Y. et al. Enhanced chemical stability of VO₂ nanoparticles by the formation of SiO₂/VO₂ core/shell structures and the application to transparent and flexible VO₂-based composite foils with excellent thermochromic properties for solar heat control. *Energy Environ. Sci.* **5**, 6104–6110 (2012).
96. Truby, R. L. & Lewis, J. A. Printing soft matter in three dimensions. *Nature* **540**, 371–378 (2016).
97. Castro, J. O., Ramesan, S., Rezk, A. R. & Yeo, L. Y. Continuous tuneable droplet ejection via pulsed surface acoustic wave jetting. *Soft Matter* **14**, 5721–5727 (2018).
98. Ji, H., Liu, D., Cheng, H. & Tao, Y. Large area infrared thermochromic VO₂ nanoparticle films prepared by inkjet printing technology. *Sol. Energy Mater. Sol. Cells* **194**, 235–243 (2019).
99. Patil, R. A., Devan, R. S., Liou, Y. & Ma, Y.-R. Efficient electrochromic smart windows of one-dimensional pure brookite TiO₂ nanoneedles. *Sol. Energy Mater. Sol. Cells* **147**, 240–245 (2016).
100. Kerszulis, J. A., Amb, C. M., Dyer, A. L. & Reynolds, J. R. Follow the yellow brick road: structural optimization of vibrant yellow-to-transmissive electrochromic conjugated polymers. *Macromolecules* **47**, 5462–5469 (2014).
101. Bera, M. K., Mori, T., Yoshida, T., Ariga, K. & Higuchi, M. Construction of coordination nanosheets based on Tris (2, 2'-bipyridine)-Iron (Fe²⁺) complexes as potential electrochromic materials. *ACS Appl. Mater. Interfaces* **11**, 11893–11903 (2019).
102. Qian, J., Ma, D., Xu, Z., Li, D. & Wang, J. Electrochromic properties of hydrothermally grown Prussian blue film and device. *Sol. Energy Mater. Sol. Cells* **177**, 9–14 (2018).
103. Rosseinsky, D.R., Monk, P.M. & Mortimer, R. J. *Electrochromic materials and devices* (John Wiley & Sons, 2015).
104. Sang, J. et al. Smart Windows with a VO₂ Thin Film as a Conductive Layer for Efficient and Independent Dual-Band Modulation, *ACS Appl. Electron. Mater* **3**, 4882–4890 (2021).
105. Benson, D. K. et al. In *Advanced Sensors and Monitors for Process Industries and the Environment*. (SPIE, 1999).
106. Korman, V. In *Society of Photo-Optical Instrumentation Engineers (SPIE) Conference Series*, (SPIE, 2006).
107. Georg, A., Graf, W., Neumann, R. & Wittwer, V. Mechanism of the gasochromic coloration of porous WO₃ films. *Solid State Ion.* **127**, 319–328 (2000).
108. Georg, A., Graf, W., Neumann, R. & Wittwer, V. Stability of gasochromic WO₃ films. *Sol. Energy Mater. Sol. Cells* **63**, 165–176 (2000).
109. Calvino, C., Neumann, L., Weder, C. & Schrettli, S. Approaches to polymeric mechanochromic materials. *J. Polym. Sci. Part A: Polym. Chem.* **55**, 640–652 (2017).
110. Jiang, B., Liu, L., Gao, Z. & Wang, W. A general and robust strategy for fabricating mechanoresponsive surface wrinkles with dynamic switchable transmittance. *Adv. Optical Mater.* **6**, 1800195 (2018).
111. Shrestha, M., Asundi, A. & Lau, G.-K. Smart window based on electric unfolding of microwrinkled TiO₂ nanometric films. *ACS Photonics* **5**, 3255–3262 (2018).
112. Ke, Y. et al. Smart windows: electro-, thermo-, mechano-, photochromics, and beyond, *Advanced Energy. Materials* **9**, 1902066 (2019).
113. Ke, Y. et al. Cephalopod-inspired versatile design based on plasmonic VO₂ nanoparticle for energy-efficient mechano-thermochromic windows. *Nano Energy* **73**, 104785 (2020).
114. Harada, J., Taira, M. & Ogawa, K. Photochromism of Fulgide Crystals: From Lattice-Controlled Product Accumulation to Phase Separation. *Cryst. Growth Des.* **17**, 2682–2687 (2017).
115. Irie, M., Fukaminato, T., Matsuda, K. & Kobatake, S. Photochromism of Diarylethene Molecules and Crystals: Memories, Switches, and Actuators. *Chem. Rev.* **114**, 12174–12277 (2014).
116. Xia, H., Xie, K. & Zou, G. Advances in spiropyrans/spirooxazines and applications based on fluorescence resonance energy transfer (FRET) with fluorescent materials. *Molecules* **22**, 2236 (2017).
117. Schrauben, J. N. et al. Titanium and zinc oxide nanoparticles are proton-coupled electron transfer agents. *Science* **336**, 1298–1301 (2012).
118. Sato, O. Optically switchable molecular solids: photoinduced spin-crossover, photochromism, and photoinduced magnetization. *Acc. Chem. Res.* **36**, 692–700 (2003).
119. Pardo, R., Zayat, M. & Levy, D. Photochromic organic-inorganic hybrid materials. *Chem. Soc. Rev.* **40**, 672–687 (2011).
120. Minkin, V. I. Photo-, thermo-, solvato-, and electrochromic spiroheterocyclic compounds. *Chem. Rev.* **104**, 2751–2776 (2004).
121. Zhao, X. et al. VO₂-based composite films with exemplary thermochromic and photochromic performance. *J. Appl. Phys.* **128**, 185107 (2020).
122. Fu, F. & Hu, L. In *Advanced High Strength Natural Fibre Composites in Construction*, (eds Fan, M., and Fu, F.) 405–423 (Woodhead Publishing, 2017).
123. Zhang, Y. et al. Perovskite thermochromic smart window: Advanced optical properties and low transition temperature. *Appl. Energy* **254**, 113690 (2019).
124. Saito, M. A cross-cultural study on color preference in three asian cities comparison between Tokyo, Taipei and Tianjin. *Jpn. Psychol. Res.* **36**, 219–232 (1994).
125. Mofarah, M. Y., Tahmtan, Z. S., Dadashi, M. T. & Banihashemian, S. H. How color affects marketing, *Arab. J. Bus. Manag. Rev. (Oman Chap.)* **34**, 1–9 (2013).
126. Lu, C. et al. Nanoparticle-free and self-healing amphiphobic membrane for anti-surfactant-wetting membrane distillation. *J. Environ. Sci.* **100**, 298–305 (2021).
127. Su, C. et al. Robust superhydrophobic membrane for membrane distillation with excellent scaling resistance. *Environ. Sci. Technol.* **53**, 11801–11809 (2019).
128. Lin, K.-T. et al. Highly efficient flexible structured metasurface by roll-to-roll printing for diurnal radiative cooling. *eLight* **3**, 22 (2023).
129. Zhu, Y. et al. Night-time radiative warming using the atmosphere. *Light Sci. Appl.* **12**, 268 (2023).
130. Qin, B., Zhu, Y., Zhou, Y., Qiu, M. & Li, Q. Whole-infrared-band camouflage with dual-band radiative heat dissipation. *Light Sci. Appl.* **12**, 246 (2023).
131. Liao, Y., Fan, Y. L. & Lei, D. Y. Thermally tunable binary-phase VO₂ metasurfaces for switchable holography and digital encryption. *Nanophotonics* **13**, 1109–1117 (2024).
132. Pei, R. et al. The valence conversion mechanism for Mo-doped VO₂ films with enhanced thermochromic properties. *Z. Anorg. Allg. Chem.* **648**, e202200132 (2022).
133. Wu, J. et al. Regulation of phase transition temperature and preparation for doping-VO₂ smart thermal control films. *J. Appl. Phys.* **131**, 085101 (2022).
134. Ersundu, A. E., Çelikkilek Ersundu, M., Doğan, E. & Güven, M. B. A comparative investigation on thermal, structural and optical properties of W and Nb-doped VO₂-based thermochromic thin films. *Thin Solid Films* **700**, 137919 (2020).
135. Zhao, C. et al. Nb-doped VO₂ single crystal microtube arrays. *Vacuum* **203**, 111309 (2022).
136. Dietrich, M. K., Kuhl, F., Polity, A. & Klar, P. J. Optimizing thermochromic VO₂ by co-doping with W and Sr for smart window applications. *Appl. Phys. Lett.* **110**, 141907 (2017).
137. Kuhl, F. et al. Embedding Quaternary V_{1-x-y}Sr_xW_yO₂ into Multilayer Systems to Enhance Its Thermochromic Properties for Smart Glass Applications. *ACS Appl. Electron. Mater.* **4**, 513–520 (2022).
138. Guo, H., Wang, Y., Jain, A., Fu, H. & Chen, F. Preparation of W/Zr co-doped VO₂ with improved microstructural and thermochromic properties. *J. Alloy. Compd.* **878**, 160352 (2021).
139. Haji, H. F. et al. Zr and W Co-doped VO₂ thin films with improved luminous transmittance and transition temperature. *J. Mater. Sci.: Mater. Electron.* **34**, 2006 (2023).
140. Lv, W., Huang, D., Chen, Y., Qiu, Q. & Luo, Z. Synthesis and characterization of Mo-W co-doped VO₂ (R) nano-powders by the microwave-assisted hydrothermal method. *Ceram. Int.* **40**, 12661–12668 (2014).
141. Jiazhen, Y., Yue, Z., Wanxia, H. & Mingjin, T. Effect of Mo-W Co-doping on semiconductor-metal phase transition temperature of vanadium dioxide film. *Thin Solid Films* **516**, 8554–8558 (2008).
142. Zhao, Z. et al. Sn-W Co-doping Improves Thermochromic Performance of VO₂ Films for Smart Windows. *ACS Appl. Energy Mater.* **3**, 9972–9979 (2020).
143. Li, P. et al. Enhancing thermochromic properties of VO₂ amorphous films on glass substrates by Sn-W co-doping. *Infrared Phys. Technol.* **134**, 104871 (2023).
144. Gao, Y. et al. Phase and shape controlled VO₂ nanostructures by antimony doping. *Energy Environ. Sci.* **5**, 8708–8715 (2012).
145. Cui, Y. et al. First-principles study of phase-transition temperature and optical properties of alkaline earth metal (Be, Mg, Ca, Sr or Ba)-doped VO₂. *Ceram. Int.* **44**, 20814–20820 (2018).
146. Zou, Z. et al. Thermochromic, threshold switching, and optical properties of Cr-doped VO₂. *thin films, J. Alloy. Compd.* **806**, 310–315 (2019).
147. Suleiman, A. O., Mansouri, S., Margot, J. & Chaker, M. Tuning VO₂ phase stability by a combined effect of Cr doping and oxygen pressure. *Appl. Surf. Sci.* **571**, 151267 (2022).

148. Gu, D., Zheng, H., Ma, Y., Xu, S. & Zhou, X. A highly-efficient approach for reducing phase transition temperature of VO₂ polycrystalline thin films through Ru⁴⁺-doping. *J. Alloy. Compd.* **790**, 602–609 (2019).
149. GGui, X. & Cava, R. J. Metal-insulator transition and anomalous lattice parameters changes in Ru-doped VO₂. *Phys. Rev. Mater.* **6**, 075005 (2022).
150. Qi, J., Ning, G. & Lin, Y. Synthesis, characterization, and thermodynamic parameters of vanadium dioxide. *Mater. Res. Bull.* **43**, 2300–2307 (2008).
151. Ye, J. et al. Preparation, characterization and properties of thermochromic tungsten-doped vanadium dioxide by thermal reduction and annealing. *J. Alloy. Compd.* **504**, 503–507 (2010).
152. Zhang, H. et al. A cost-effective method to fabricate VO₂ (M) nanoparticles and films with excellent thermochromic properties. *J. Alloy. Compd.* **636**, 106–112 (2015).
153. Jung, D., Kim, U. & Cho, W. Fabrication of pure monoclinic VO₂ nanoporous nanorods via a mild pyrolysis process. *Ceram. Int.* **44**, 6973–6979 (2018).
154. Billik, P. et al. Synthesis and transport properties of nanostructured VO₂ by mechanochemical processing. *Meas. Sci. Rev.* **11**, 29 (2011).
155. Wang, C. et al. One-step ball milling synthesis of VO₂ (M) nanoparticles with exemplary thermochromic performance. *SN Appl. Sci.* **3**, 436 (2021).
156. Rama, N. & Ramachandra Rao, M. S. Synthesis and study of electrical and magnetic properties of vanadium oxide micro and nanosized rods grown using pulsed laser deposition technique. *Solid State Commun.* **150**, 1041–1044 (2010).
157. Florian Aguilar, C. A. Fabricación de películas delgadas de óxido de vanadio por el método sputtering como material termocrómico, (2015).
158. Kim, M. H. et al. Growth of Metal Oxide Nanowires from Supercooled Liquid Nanodroplets. *Nano Lett.* **9**, 4138–4146 (2009).
159. Devthade, V. & Lee, S. Synthesis of vanadium dioxide thin films and nanostructures. *J. Appl. Phys.* **128**, 231101 (2020).
160. Li, Y., Jiang, P., Xiang, W., Ran, F. & Cao, W. A novel inorganic precipitation-peptization method for VO₂ sol and VO₂ nanoparticles preparation: Synthesis, characterization and mechanism. *J. Colloid Interface Sci.* **462**, 42–47 (2016).
161. Chen, H.-K., Hung, H.-C., Yang, T. C. K. & Wang, S.-F. The preparation and characterization of transparent nano-sized thermochromic VO₂-SiO₂ films from the sol-gel process. *J. Non-Crystalline Solids* **347**, 138–143 (2004).
162. Cao, C., Gao, Y. & Luo, H. Pure single-crystal rutile vanadium dioxide powders: Synthesis, mechanism and phase-transformation property, The. *J. Phys. Chem. C.* **112**, 18810–18814 (2008).
163. Pham, V.-H. et al. Microstructure and luminescence of VO₂ (B) nanoparticle synthesis by hydrothermal method. *Green. Process. Synth.* **8**, 802–807 (2019).
164. Whittaker, L., Velazquez, J. M. & Banerjee, S. A VO-seeded approach for the growth of star-shaped VO₂ and V₂O₅ nanocrystals: facile synthesis, structural characterization, and elucidation of electronic structure. *CrystEngComm* **13**, 5328–5336 (2011).
165. Zhong, L. et al. TiO₂ seed-assisted growth of VO₂ (M) films and thermochromic performance. *CrystEngComm.* **18**, 7140–7146 (2016).
166. Wu, H. et al. Direct synthesis of vanadium oxide nanopowders by the combustion approach. *Chem. Phys. Lett.* **706**, 7–13 (2018).
167. Cao, Z. et al. A simple and low-cost combustion method to prepare monoclinic VO₂ with superior thermochromic properties. *Sci. Rep.* **6**, 39154 (2016).
168. Cao, X., Jin, P. & Luo, H. In Nanotechnology in Eco-Efficient Construction. 503–524 (Elsevier, 2019).
169. Whittaker, L., Patridge, C. J. & Banerjee, S. Microscopic and nanoscale perspective of the metal–insulator phase transitions of VO₂: some new twists to an old tale. *J. Phys. Chem. Lett.* **2**, 745–758 (2011).
170. He, X. et al. Orbital change manipulation metal–insulator transition temperature in W-doped VO₂. *Phys. Chem. Chem. Phys.* **17**, 11638–11646 (2015).
171. Ji, H., Liu, D., Zhang, C. & Cheng, H. VO₂/ZnS core-shell nanoparticle for the adaptive infrared camouflage application with modified color and enhanced oxidation resistance. *Sol. Energy Mater. Sol. Cells* **176**, 1–8 (2018).
172. Kim, Y. et al. High-throughput roll-to-roll fabrication of flexible thermochromic coatings for smart windows with VO₂ nanoparticles. *J. Mater. Chem. C.* **6**, 3451–3458 (2018).
173. Chen, Y. et al. High performance and enhanced durability of thermochromic films using VO₂@ZnO core–shell nanoparticles. *ACS Appl. Mater. Interfaces* **9**, 27784–27791 (2017).
174. Zhang, Q., Sando, D. & Nagarajan, V. Chemical route derived bismuth ferrite thin films and nanomaterials. *J. Mater. Chem. C.* **4**, 4092–4124 (2016).
175. Pujahari, R. In Energy Materials. 27–60 (Elsevier, 2021).
176. SpinCoater, WHAT IS SPIN COATING? <https://www.spincoater.com/what-is-spin-coating.php>. Accessed 2019).
177. Siemann, U. In Scattering methods and the properties of polymer materials. 1–14 (Springer, 2005).
178. Jabari, E. et al. 2D printing of graphene: a review. *2D Mater.* **6**, 042004 (2019).
179. Sheng, M., Wang, W., Li, L., Zhang, L. & Fu, S. All-in-one wearable electronics design: Smart electrochromic liquid-crystal-clad fibers without external electrodes. *Colloids Surf. A: Physicochemical Eng. Asp.* **630**, 127535 (2021).
180. Gao, C. et al. A review on WO₃ gasochromic film: Mechanism, preparation and properties. *Int. J. Hydrogen Energy* **48**, 2442–2465 (2022).
181. Imato, K. et al. Mechanochromic dynamic covalent elastomers: quantitative stress evaluation and autonomous recovery. *ACS Macro Lett.* **4**, 1307–1311 (2015).